



**VYCOM<sup>®</sup>**

**CELTEC<sup>®</sup>**

**USER MANUAL**

---

HOW-TO GUIDE

---

No part of this publication may be reproduced, stored in a retrieval system, or transmitted in any form or by any means, mechanical, electronics, photocopying, recording, or otherwise, without prior written permission of Vycom.

**Vycom**

801 E. Corey Street  
Scranton, PA 18505

**P:** 800-235-8320

**F:** 800-858-9266

[www.vycomplastics.com](http://www.vycomplastics.com)

Celtec is a registered trademark of Vycom.

© 2023 by Vycom All Rights Reserved.

All information contained herein is accurate to the best of our knowledge and is provided without liability or commitment whatsoever. All recommendations or suggestion are made without guarantee since the conditions of use are beyond our control. We recommend that you confirm the suitability of our product by carrying out tests under your local conditions and using your own mechanical equipment.

We disclaim any liability incurred in connection with the use of these data or suggestions. This publication is not to be taken as a license to operate under or a recommendation to infringe any patents. The observance of all legal regulations and patents is the responsibility of the user.

Processing and finishing techniques are presented as “typical.” Information contained herein is considered accurate to the best of our knowledge. It is offered for your consideration and investigation and is not to be construed as a representation or warranty, expressed or implied, for which Vycom assumes any legal responsibility. Our warranties are limited to those expressly stated in the written contracts or in conditions of sale. As conditions and methods of use vary and are beyond the control of Vycom, Vycom disclaims any liability incurred as a result of the use of its products in accordance with the data contained on our physical properties charts or in our manual. No information herein shall be construed as an offer of indemnity for infringement or as a recommendation to use the products in such a manner as to infringe any patent, domestic or foreign.

# TABLE OF CONTENTS

CELTEC®

4	<a href="#">Contents</a>	35	<a href="#">Pressure or Drape Forming</a>
5	<a href="#">Introduction</a>	37	<a href="#">Vacuum Forming</a>
7	<a href="#">Product Availability</a>	37	<a href="#">Heat Welding</a>
		39	<a href="#">Manufacturers</a>
9	<b><a href="#">Chapter 1: Processing</a></b>	42	<b><a href="#">Chapter 4: Graphics Applications</a></b>
9	<a href="#">Handling</a>	42	<a href="#">Cleaning/Pretreating</a>
9	<a href="#">Cutting</a>	43	<a href="#">Digital Flatbed Printing</a>
10	<a href="#">Die Cutting</a>	44	<a href="#">Painting/Varnishing</a>
18	<a href="#">Sawing</a>	45	<a href="#">Surface Prep</a>
19	<a href="#">Drilling</a>	46	<a href="#">Cross-Hatch Adhesion Test</a>
19	<a href="#">Milling</a>	48	<a href="#">Vinyl Lettering</a>
20	<a href="#">Routing</a>	48	<a href="#">Manufacturers</a>
20	<a href="#">Edge Finishing</a>	52	<b><a href="#">Chapter 5: Special Applications</a></b>
20	<a href="#">Laser Cutting</a>	52	<a href="#">Photo Mounting</a>
20	<a href="#">Waterjet Cutting</a>	53	<a href="#">Laminating</a>
21	<a href="#">Manufacturers</a>	55	<a href="#">Laminating Techniques</a>
23	<b><a href="#">Chapter 2: Fastening</a></b>	61	<a href="#">Manufacturers</a>
23	<a href="#">Notch Sensitivity</a>	62	<b><a href="#">Chapter 6: Engineering Specifications</a></b>
23	<a href="#">Thermal Expansion/Contraction</a>	62	<a href="#">Weatherability</a>
27	<a href="#">Screwing and Nailing</a>	63	<a href="#">Fire Characteristics</a>
28	<a href="#">Installation</a>	64	<a href="#">Standard Specifications</a>
29	<a href="#">Bonding and Adhesives</a>	66	<a href="#">Celtec Typical Physical Properties</a>
30	<a href="#">Adhesives and Manufacturers</a>	68	<b><a href="#">Chapter 7: Celtec Resources</a></b>
34	<b><a href="#">Chapter 3: Forming/Welding</a></b>	68	<a href="#">Material Safety Data</a>
34	<a href="#">Heat Bending</a>	68	<a href="#">Marketing Communication</a>
		69	<a href="#">Sustainability</a>

# INTRODUCTION

## CELTEC®

Celtec® is a lightweight, expanded foam polyvinyl chloride (PVC) sheet material manufactured by Vycom that combines the chemical resistance and fabrication capabilities of rigid PVC with a closed cell expanded core.

Vycom introduced Celtec in 1987 primarily for the graphics market. Today, our increased capacity allows us to manufacture Celtec in gauges from 1mm through 38mm for use in an expanding variety of markets. The structure of Celtec is a closed cell foam that does not absorb moisture. These features combined with its lighter weight and insulating characteristics (sound and thermal) to make Celtec the choice material for high traffic and harsh environments, both interior and exterior.

Celtec has a high-quality surface for both screen and direct Digital Printing, using the flatbed feed technology as well as painting and applying vinyl graphics. It is lightweight for easy handling. It has low flammability and good chemical resistance to meet or exceed industry standards for a wide variety of applications, including exhibits, point-of-purchase displays, signs, and theater props. Celtec applications are limited only by your imagination. We are always eager to learn about new and exciting applications. **Please contact Vycom if you discover a creative new use of Celtec.**  
[www.vycomplastics.com/about/contact-us](http://www.vycomplastics.com/about/contact-us)

The inherent properties of Celtec eliminate time-consuming and costly surface preparation. In addition, the material can easily be cut, joined, and fabricated with a wide variety of adhesives and ordinary fasteners and using readily available hand tools. Celtec can be milled and routed like wood, and often more quickly. Because there are no knots, there is little likelihood of voids or holes in the mid-wall. Celtec is free foam and therefore does not have the inherent problems of voids that may be present in sheets manufactured using the Celuka process. Celtec has a microscopic cell structure, enabling superior edge finishing and routing. By varying the feed rates and speeds, you can attain a very smooth edge. When an even smoother edge is necessary, sanding and painting can be performed, as can laminating edge finishing.

Celtec also offers superior thermal properties and low-thermal conductivity, along with high insulation and sound-absorption qualities. See the Engineering Specifications section of this manual for detailed information.

As a rigid and lightweight foamed PVC sheet, Celtec is excellent for the highly specialized needs of producing signage and displays as well as booths and stage sets. Other applications include photo mounting and building materials. Celtec is USDA approved for incidental contact “wherever food is processed or sold.” Celtec is free of lead, barium, and cadmium. And, as the first foamed PVC to be U.L. Classified, Celtec meets all three U.L. 1975 fire test requirements, minimizing the risk of both head conduction and fire.

Vycom, an affiliate of The AZEK Company, manufactures market-leading brands of highly innovative plastic sheet products designed to replace wood, metal, and other traditional materials in a variety of applications. The company's extensive inventory and product offerings provide its customers with the convenience of single source purchasing and the ability to maximize efficiency. Vycom's manufacturing agility places it in a prime position to be the essential partner in creating solutions that optimize quality and performance and in providing a more sustainable future. For more information, visit [www.vycomplastics.com](http://www.vycomplastics.com).

# PRODUCT AVAILABILITY

CELTEC®

Custom colors, sizes, gauges, tolerances, and formulations are available upon request and with a minimum order quantity. Actual color may vary from production run to production run. Due to limitations in printing, precise color may differ from samples shown below.

<b>NOTE!</b>		PMS and other color-coding systems are listed below as an approximation to provide designers with a color range. Actual colors may differ from printed samples shown below. Physical samples are available upon request.				
Color	Sample	PMS	RGB	CMYK		HEX #
White		0	R: 255 G: 255 B: 255	C: 0 M: 0	Y: 0 K: 0	#FFFFFF
Black		Black	R: 0 G: 0 B: 0	C: 0 M: 0	Y: 0 K: 100	#000000
Gray		Gray 8C	R: 140 G: 140 B: 140	C: 0 M: 0	Y: 0 K: 45	#8C8C8C
Stone		Cool Gray 4	R: 204 G: 204 B: 198	C: 0 M: 0	Y: 3 K: 20	#CCCCCC
Beige		Beige 400	R: 208 G: 193 B: 164	C: 18 M: 19	Y: 27 K: 0	#D0C1A4
Yellow		Yellow 123	R: 252 G: 198 B: 16	C: 1 M: 22	Y: 95 K: 0	#FCC610
Green		Green 355	R: 39 G: 154 B: 55	C: 85 M: 0	Y: 95 K: 0	#1D9A37
Red		Red 703	R: 192 G: 0 B: 15	C: 0 M: 100	Y: 85 K: 24	#C0000F
Blue		Blue 653	R: 17 G: 22 B: 134	C: 100 M: 87	Y: 0 K: 0	#111686

Color	Available Thickness (metric) / Sheet Sizes (inches) - Standard Sizes (as of October 2023; subject to change)													
	1mm	2mm	3mm	4mm	5mm	6mm	10mm	12mm	15mm	19mm	25mm	30mm	32mm	38mm
White	49 x 97	48 x 96 48 x 120 60 x 120	48 x 96* 48 x 120 50 x 100 60 x 96 60 x 120	48 x 96	48 x 96	48 x96* 48 x120 60 x96 60 x120	48 x 96 48 x 120 60 x 120	48 x 96 48 x 120 60 x 120	48 x 96 48 x 120	48 x 96 48 x 120 60 x 120	48 x 96 48 x 120 60 x 120	48 x 96 48 x 120	48x96	48x96
Vivid White		48 x 96 60 x 120	48 x 96 48 x 120 60 x 96 60 x 120	48 x 96	48 x 96	48 x 96 48 x 120 60 x 96 60 x 120	48 x 96 48 x 120	48 x 96 48 x 120 60 x 120	48 x 96 60 x 120	48 x 96 48 x 120 60 x 96 60 x 120	48 x 96 48 x 120 60 x 96 60 x 120			
Black		48 x 96	48 x 96 48 x 120 60 x 96 60 x 120		48 x 96	48 x 96 48 x 120 60 x 96 60 x 120	48 x 96	48 x 96 60 x 120	48 x 96 60 x 120	48 x 96 48 x 120 60 x 96 60 x 120	48 x 96 48 x 120 60 x 96 60 x 120			
Gray			48 x 96			48 x96	48 x 96	48 x 96						
Stone			48 x 96			48 x96								
Beige			48 x 96			48 x96								
Yellow			48 x 96			48 x96								
Green			48 x 96			48 x96								
Red			48 x 96			48 x96								
Blue			48 x 96			48 x96								
Ultra White		48 x 96*	48 x 96*			48 x96*								
DigiLite (White)			48x96 48x120 60x96 60x120			48x96 48x120 60x96 60x120								
DigiLite (Black)			48x96 48x120 60x96 60x120			48x96 48x120 60x96 60x120								
Wood Grain							48x96 (9mm)	48x96		48x96				



# PROCESSING

CELTEC®

# 1

This chapter details various methods of fabricating Celtec as part of processing the material into its final form. Common metal and woodworking tools and machinery can be used, depending on the specific application for the finished product.

## Handling

Celtec material should be ordered in bulk and remain untouched. Celtec material should be properly stored in a clean, cool, dust-free, controlled environment.

All Celtec material, if cleaning is necessary, should be cleaned the same way using alcohol, either with isopropyl or denatured, and wiped thoroughly in one direction.

Human hands contain oils and acids that alter the print characteristics of a substrate. Oils will alter the print surface by lowering the surface tension / dyne level, which results in flaws on print that resemble lighter ink areas in the shape of

fingerprints. Acids will etch into the materials and, over time, will cause a tiny recess in the material surface as the acid eats part of the substrate away. Recent fingerprints can be easily wiped off with alcohol, either with isopropyl or denatured, and wiped thoroughly in one direction. Older fingerprints cannot be wiped off because of the physical and chemical changes they have caused on the surface of the substrate. All personnel (manufacturer, distributor, shipper, material handler, etc.) that handles the substrate prior to printing should wear clean cotton gloves.



## Cutting

Sheets of Celtec up to 3mm thick can be cut with a utility knife. To cut sheets thicker than 3mm, band saws, table saws, and panel saws can be used, as detailed in this chapter. Power sheers and guillotines can crush the edges of Celtec sheets over 4mm and can produce unacceptable results.

With any cutting procedure, friction heat can build up and produce unacceptable results on cut edges. Rough edges can also occur from cutting the Celtec using inadequate support or from using worn or improper tooling. For best results, test the machine setups and cutting processes before beginning production.

**NOTE!**

Celtec's density is approximately half the density of conventional PVC, which makes it compress relatively easily.

## Die Cutting

When Celtec sheets are used for mass-producing flat shapes or cutouts, die cutting is the most commonly used fabrication technique. Celtec is an ideal material for die cutting, producing a clean, smooth edge without splintering or cracking. Die cutting is recommended for a wide range of applications, including letters, openings within larger sheets of Celtec, puzzle pieces, and assemblies that fold into three-dimensional shapes, such as point-of-purchase (POP) displays (Figure 1a).

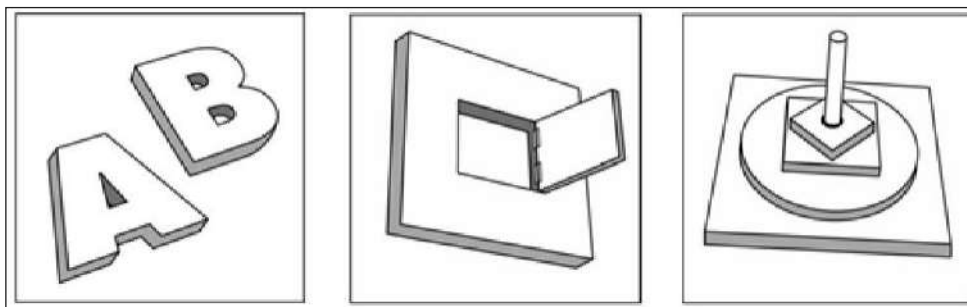


Figure 1a

To improve processing efficiency, Celtec sheets can be painted, printed, or silkscreened prior to die cutting. After die cutting, the Celtec sheets or pieces can be finished by heat bending, fastening, gluing, or machining.

**NOTE!**

Test the die cut suitability of the Celtec material before painting or silk-screening an entire production run. Select proper inks and paints for die cutting.

# PROCESSING

## CELTEC®

Of the various die cutting methods available, the most frequently used method is Steel Rule Die Cutting, in which the steel rule die (SRD) functions very much like a cookie cutter.

SRDs are constructed from one-inch-wide strip steel, available in 500-foot coils, with one pre-sharpened edge. The thickness of the strip steel can be specified by a **point** designation, with one point equaling 0.014". To cut Celtec with an SRD, the recommended thickness of strip steel ranges from 2 points (0.028") to 6 points (0.084"). The most commonly used strip steel thicknesses for cutting Celtec are 3 points (0.042") and 4 points (0.054").

To construct the die, lengths of strip steel are first cut from the coil. These cut lengths called knives are then bent to the desired shape or pattern to be cut and embedded in a maple block called a die body.

The SRD assembly is mounted under the top platen of the press. The Celtec sheet is then placed on a steel bottom platen. When pressure is applied, the knives of the SRD are forced through the Celtec, producing a **cut**.

Hydraulic platens, or "clicker" presses, are used to supply the necessary pressure for the cut. After the cut, the platens are separated, and the sheet or cutouts are removed. At this point, any finishing work required can begin.

To help eject the cut Celtec, strips of a resilient, compressible material, such as open cell foam rubber, can be glued next to the knives (Figure 1b). The strips should extend about 1/16" beyond the cutting edge of the knife. Strips of the same material can be used to secure the sheet in position by gluing the strips to the top or bottom platen of the press.

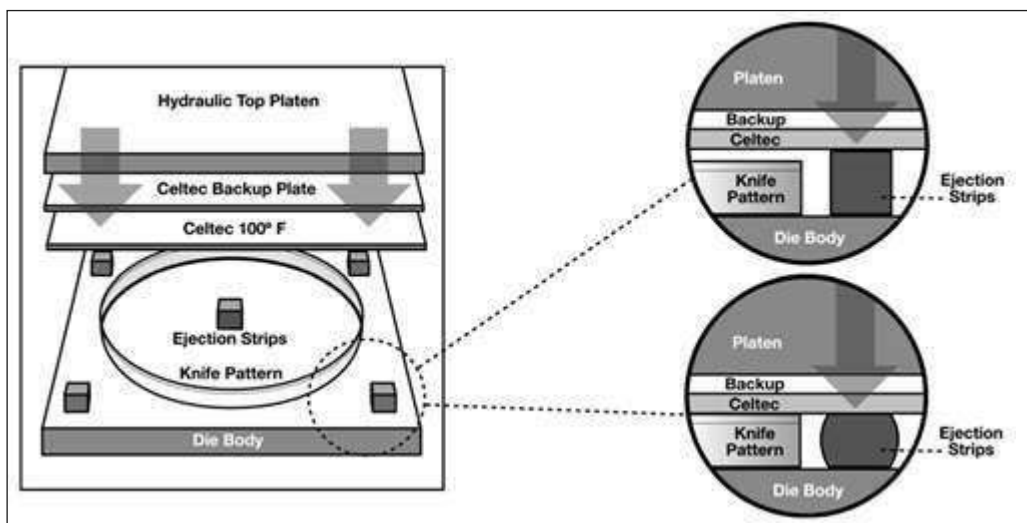


Figure 1b

**NOTE!**

For best results, dull or worn knives should be replaced as needed with new ones.

**Factors affecting die cutting quality:**

**Temperature of the Celtec Material:** Celtec is a thermoplastic, which means it tends to be more brittle at lower temperatures. When the Celtec sheet temperature is below 75°F, the first two-thirds of the cut is clean while the last third exhibits fracturing. When the Celtec material is heated above 75°F, the quality of the cut improves, which reduces fracturing. The best result is achieved when Celtec is preheated to a temperature between 100°F and 130°F.

**TIP**

For complex die cut parts, utilizing a higher temperature during cutting will reduce the likelihood that fracturing of the Celtec will occur.

**Sheet Thickness:** The quality of the die cut is also affected by the material's thickness. The best cuts are produced using Celtec sheets of 3mm or less. Die cuts in Celtec sheets over 4mm tend to exhibit deformation, roughness along the cut edge, and/or fractures in the material. To cut Celtec:

1. Verify that the SRD has the proper point value and bevel.
2. Preheat the material to 100°F.
3. Select the appropriate backup plate.
4. Maintain a sharp cutting edge.

For material over 4mm thick, additional steps, such as sanding or routing, may be necessary after die cutting to smooth any rough edges produced by the cut.

The thickness of the Celtec material will also affect the quality of the die cut when the piece has one or more small radii. As the thickness increases, the difficulty involved in producing smooth cuts with small radii also increases. Sheets 4mm thick or less can be die cut using a radius as small as 1/8".

# PROCESSING

## CELTEC®

**Knife Thickness:** As the knife edge penetrates the Celtec, it exerts an enormous compressive force that can produce deformation, or rounding, of the material's corners. The knife's penetration also creates a shearing force which tends to cause fracturing of the material approximately two-thirds of the way through the Celtec sheet. Applications that require cutting of narrow radii or U-shaped tabs are highly susceptible to shearing because of the severe lateral pressure.

The selection of a correct gauge (point thickness) for the knife material is critical for any die cutting operation. For example, straighter, smoother cuts involving small radii are more readily achieved using a thinner rather than thicker gauge knife steel, assuming that both knives have the same bevel configuration and angle. However, a thinner knife is more vulnerable to warping, bending, or breaking because of the extreme compression when the Celtec is thick, especially when the sheet is below 100°F.

### TIP

A thinner gauge knife will not require as high a sheet temperature to produce equivalent quality die cuts because a thinner knife encounters less resistance and creates a cleaner edge on the cut Celtec. A thicker knife will require that the Celtec be heated to make it more flexible and less brittle in order to create a similar die cut quality.

The appropriate die knife thickness is directly related to the thickness of the Celtec material being cut. If the knife is too thin for the thickness of the Celtec, the knife is prone to breaking. If it is too thick, the knife tends to deform the Celtec material.

When die cutting Celtec sheets, use the following guidelines to determine the appropriate knife size:

- For most common applications, a 3-point or 4-point (0.042" or 0.056") knife is recommended.
- For cutting complex parts in sheet material less than 4mm, a 2-point (0.028") knife is recommended.
- For sheets over 6mm or for wide separating cuts, a 6-point (0.084") knife is recommended.

**Correct Bevel Selection:** Knife bevels vary according to length and type. Bevel length is defined as the distance from the tip to the end of the honed surface. When cutting Celtec, the length of the bevel should be between 3/16" and 1/4" (Figure 1c).

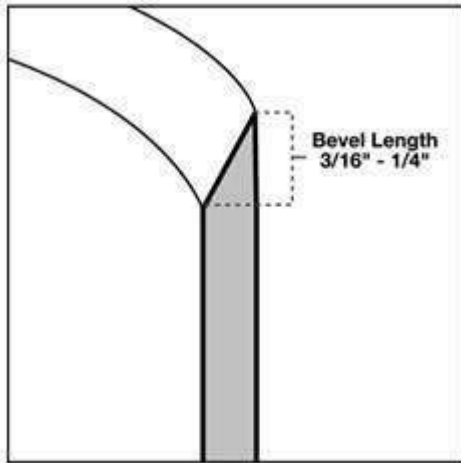


Figure 1c

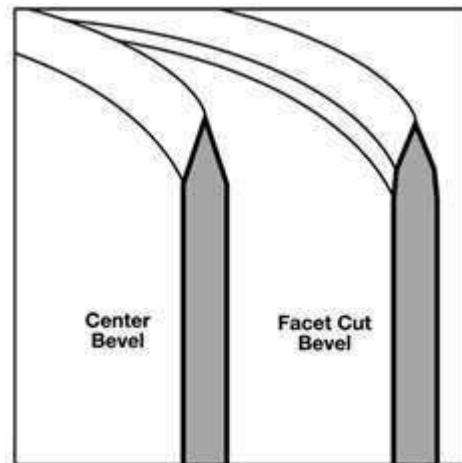


Figure 1d

The bevel can be one of three basic types: center, inside, or outside. A **center bevel** is honed from both sides, producing a V-shaped point with each leg of the V being equal. A modified center bevel, or **facet cut bevel**, is recommended for cutting Celtec. To create a facet cut bevel, the V of a center bevel is honed for a second time, giving the lead cutting edge a more obtuse angle (Figure 1d).

**TIP**

In general, the longer the length of the bevel, the smoother the resulting cut.

With either a center bevel or a facet cut bevel, the longer the bevel length and the thinner the knife, the more vertical the perimeter cut.

**TIP**

When both the inside and outside parts of a cut must be used, such as with jigsaw puzzle pieces, a center bevel is suggested because the resulting cut is wedge-shaped, thus giving both the inside and outside pieces an individual, sloped cut.

# PROCESSING

CELTEC®

An **inside bevel** has the honed side on the outside of the cut (the scrap side), while the straight, un-honed side is on the inside of the cut, or the “good side.”

An **outside bevel** reverses an inside bevel. It produces a straight cut on the inside, or good part, and a sloping cut on the outside edge, or scrap side (Figure 1e).

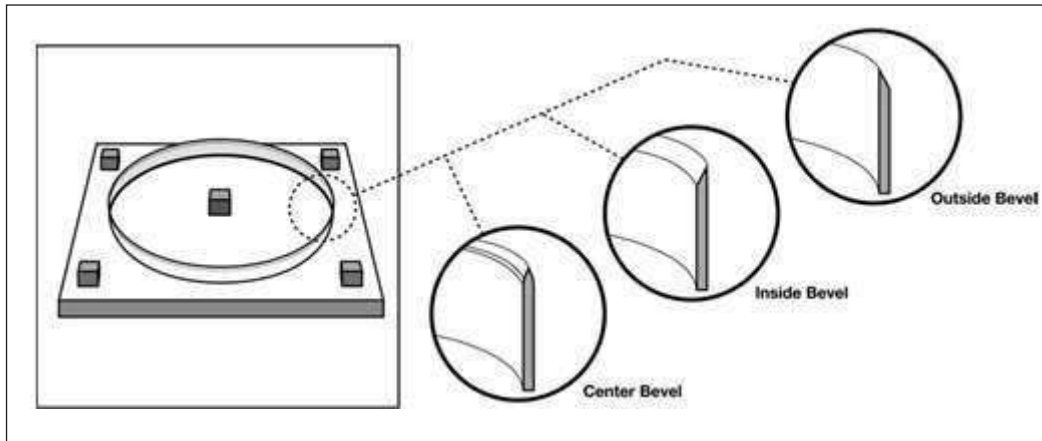


Figure 1e

**Bevel Sharpness:** Steels used for SRDs have a hardness of 57-59 Rockwell C. After much use, however, the knife will dull and produce cuts of increasingly poor quality. Re-sharpening knives is not recommended because it frequently results in an uneven edge and knife depth, even when the sharpening is performed by a skilled machinist. Even a slightly uneven edge will result in unequal penetration of the Celtec Material and thus in a ragged cut.


**TIP**

Do not re-sharpen knife blades. Always replace dull or worn knives with new ones to ensure even cuts.

**The Backup Plate:** Steel is often used to fabricate backup plates because the plate must not be too soft. However, steel plates can sometimes cause incomplete penetration of the Celtec, which also causes the material to fracture at the end of the cutting stroke. One method of avoiding this problem is to use a backup plate made from a sheet of Celtec or of chipboard placed over the steel backup plate. These softer materials enable the die to penetrate about 1/10” beyond the Celtec sheet, producing a cleaner cut (Figure 1f).

Figure 1f

**Make ready:** Due to slight variations in thickness of a backup plate, the degree of knife penetration may vary throughout the cut. In order to produce a uniform cut, the backup plate should be built up to achieve even penetration by the die. The process of building up the backup plate to eliminate unevenness is called make ready, as explained below.

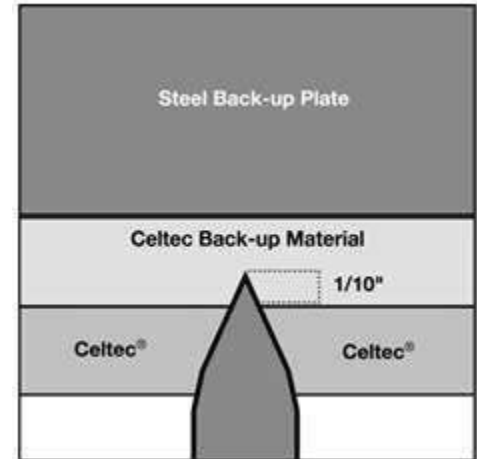

**Make ready steps for die cutting:**

1. Securely mount the SRD on the upper or lower platen as required, ensuring that it will not move during the die cutting.
2. On the opposite platen, firmly mount the die cutting plate, which should be 1/16" to 1/8" thick.
3. Using thin paper, such as Kraft wrapping paper, prepare the make ready sheet, which should be the exact size of the cutting plate. Position the make ready sheet on top of the cutting plate.

**NOTE!**

IMPORTANT! Before proceeding, make certain that the press is not out of square (Figure 1g).

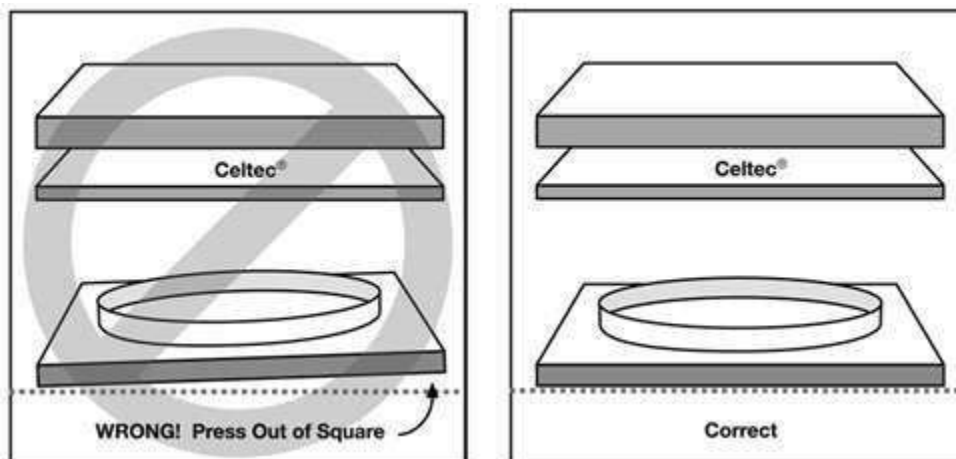


Figure 1g



# PROCESSING

## CELTEC®

4. Engage and adjust the press so that the die just touches, or “kisses,” the cutting plate. The die should leave an impression on the paper **without** leaving an impression on the plate. Usually only about two-thirds of the die pattern will leave its impression on the paper.

### TIP

Do not attempt to make a complete impression of the die cut during this step.

5. After the kiss cut, transfer the make ready sheet from the top of the cutting plate to beneath the cutting plate, taking care that it is placed in the identical position in the press. Keeping the paper in the press will ensure that the exact knife depth required to cut the Celtec cleanly, as established in Step 4 with the paper in place, is maintained (Figure 1h).

6. Place a sheet of Celtec in the press and strike a part. If, upon inspection, you find an incomplete impression, the press can be lowered. Be sure, however, that the die just contacts the cutting plate.

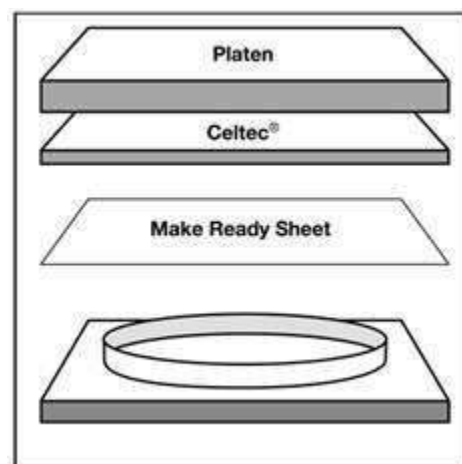


Figure 1h

7. Examine the cut Celtec. If portions of the perimeter have rough edges, follow the steps below:


- a. Remove the make ready sheet from beneath the cutting plate. Using the die-cut sample made in Step 6 as a guide, place single layers of cellophane tape on the make ready sheet in all areas where the cut is not clean. This selective taping will improve the cutting action in the problem areas.
- b. Re-insert the taped make ready sheet under the cutting plate and strike another sample, making certain that the cut just penetrates the Celtec sheet. If the cut is satisfactory, production is ready to begin. If roughly cut areas persist, repeat the taping procedure.

### NOTE!

Use a single layer of tape only. Do not overlap the tape strips or add tape to areas that are already cutting cleanly. Tape strips, or shims, may be necessary in areas in which the pattern to be die cut is intricate or has sharp bends or corners.

**Make Ready Tips:**

- When dies include intricate patterns and/or sharp bends, more pressure will be required to make the cut. Additional tape shims to build up the cutting plate may be needed in these areas (Figure 1i).
- Once the die is cutting cleanly, the make ready sheet should last throughout the entire job. If necessary, however, small imperfections can be rectified by applying additional cellophane tape to the problem areas.
- Upon completion of the job, file the make ready sheet together with the die. This will reduce setup time if the job is rerun.

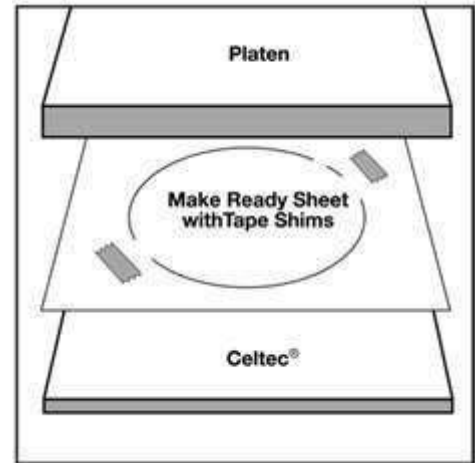**Figure 1i****NOTE!**

IMPORTANT! Do not attempt to remedy cutting problems by shimming the back of the die. It is difficult to locate the exact area for tape placement, and, in most cases, the die will wear through the tape and ruin the make ready sheet.

**Sawing**

**Circular Saws:** For Celtec sheets 3mm and thicker, carbide-tipped, triple chip ground type circular saws can be used (Figure 1j).

The following settings are recommended:

- **Rake angle:** 0° to 15°
- **Clearance angle:** 10° to 20°
- **Cutting speed:** 8,000 to 12,000 feet per minute
- **Feed:** 70 to 90 feet per minute

**Figure 1j**

**Band Saws:** High-speed steel blades normally recommended for wood or plastic (hook type) can be used for Celtec material within the following guidelines:

# PROCESSING

## CELTEC®

- 4 to 8 teeth per inch.
- Cutting speed: 3,000 to 5,000 feet per minute.
- Feed: Up to 40 feet per minute.


**Saber Saws:** Rough-cut type blades ground for plastics can be used on Celtec sheets. Smooth metal-cutting blades, however, will not produce acceptable results.

## Drilling

Celtec can be drilled with carbide-tipped bits using twist drills recommended for metals (Figure 1k). The following settings are recommended:

- Point angle: between  $90^{\circ}$  to  $110^{\circ}$
- Spiral angle:  $30^{\circ}$
- Relief angle:  $10^{\circ}$
- Cutting speed: 150 to 1,300 feet per minute
- Feed rate: 0.01" to 0.02" per revolution

Figure 1k

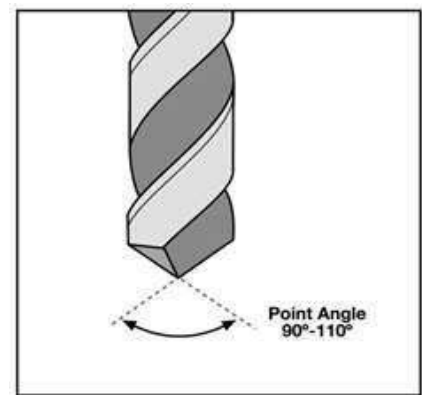

The minimum distance from the sheet edge should be two times the hole diameter. Removing the drill from the material periodically may be necessary when drilling deeper holes so that frictional heat does not build up. Drill bits ground for normal PVC will not produce acceptable results.

### TIP


For best results, drill bits should be kept sharp at all times.

## Milling

Celtec can be milled by using the following standard milling machines of various types within the following guidelines (Figure 1l):

- Relief angle:  $5^{\circ}$  to  $10^{\circ}$
- Rake angle:  $-10^{\circ}$  to  $0^{\circ}$
- Cutting speed: 3,000 to 3,500 feet per minute
- Cutting feed: 0.12" per revolution

Figure 1l

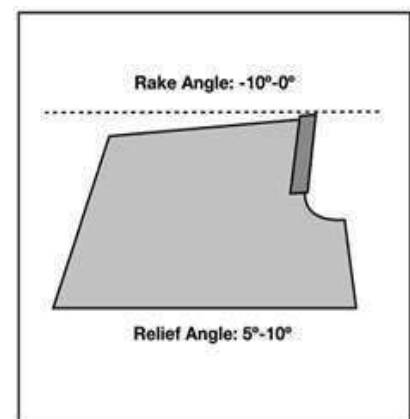

## Routing

Celtec material can be easily routed using multi-fluted carbide tools on standard woodworking routers. Standard tools and machines can be utilized without having to alter equipment bits (Figure 1m). Adjust feeds and speeds as needed to achieve the best edge finish on Celtec parts.



Figure 1m

## Edge Finishing

Edge finishing of Celtec can be accomplished using various sanding, filing, or grinding tools, such as a sander or file. Be careful not to overheat surfaces. Slight cell structure may be visible on cut edges of the Celtec material.

### TIP

**IMPORTANT!** When machining Celtec material, secure hold downs so that the force is spread out over a large area.

## Laser Cutting

Please consult the laser cutting equipment manufacturer prior to use.

## Waterjet Cutting

Celtec is easily cut using water jet equipment. Water jet offers higher tolerance accuracy, up to +/- 0.5mm, with no material waste. Multiple sheets can be stacked to obtain faster cutting times to increase machine efficiency.

# PROCESSING

CELTEC®

## Manufacturers

### Sawing Equipment

Company	Telephone	Address
Forrest Manufacturing Company <a href="http://www.forrestblades.com">www.forrestblades.com</a>	973.473.5236 / 800.733.7111 F: 973.471.3333	457 River Road Clifton, NJ 07014
Hendrick Manufacturing Corporation <a href="http://www.hendrickmanufacturing.com">www.hendrickmanufacturing.com</a>	978.741.3600 F: 978.744.0242	36 Commercial Street Salem, MA 09170
Stiles Machinery <a href="http://www.stilesmachinery.com">www.stilesmachinery.com</a>	616.698.7500 F: 616.698.9411	3965 44th Street SE Grand Rapids, MI 49512

### Die Cutting Equipment

Company	Telephone	Address
Porth Products <a href="http://www.porthproducts.com">www.porthproducts.com</a>	269.657.3985 F: 269-657-6179	56285 Fairway Drive Pawpaw, MI 49079
Preco <a href="http://www.precoinc.com">www.precoinc.com</a>	913-354-8778 F: 913-541-9088	9705 Commerce Pkwy   Lenexa, KS 66219

### Router Equipment

Company	Telephone	Address
Onsrud Cutter LP <a href="http://www.onsrud.com">www.onsrud.com</a>	800.234.1560 F: 800.557.6720	1081 S. Northpoint Boulevard Waukegan, IL 60085
Eagle America Corporation <a href="http://www.eagleamerica.com">www.eagleamerica.com</a>	800-872-2511 F: 800-872-9471	1065 Industrial Blvd South Hampton PA 18966

[This page intentionally left blank.]

# FASTENING

CELTEC®

## 2

In this chapter, various methods of fastening Celtec are covered as along with important details to consider during the fabrication process. With the numerous uses for Celtec and the differing environments of service, it is important to take into account Celtec's thermoplastic properties during fabrication and installation.

### Notch Sensitivity

When designing a Celtec part, it is important to maintain a smooth radius corner along the perimeter edge or in the slotted areas (Figure 2a). Using a sharp corner angle or scored line is not recommended and can result in fracturing of the Celtec material. With thinner sheets of Celtec, radii as small as 1/8" generally can be cut without difficulties.

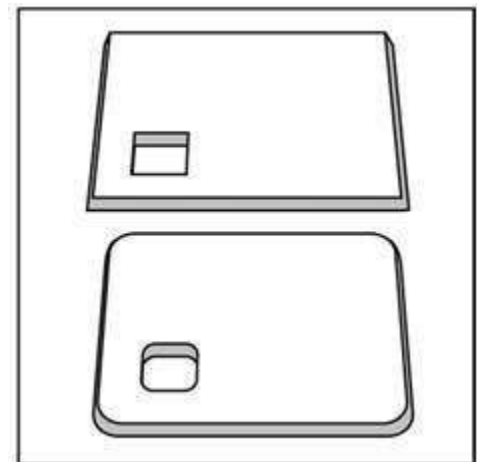


Figure 2a

### Celtec Thermal Expansion/Contraction

Because it is a cellular, or foamed, rigid polyvinyl chloride sheet product, Celtec will expand or contract with an increase or reduction in temperature, as is common with all plastic materials. When the temperature change is reversed, the material returns to its original dimensions. This property is called **linear thermal expansion and contraction**.

Because Celtec can be used in a wide variety of indoor and outdoor applications, linear thermal expansion and contraction may need to be considered during the fabrication and installation of the material. Important variables include the temperature at which the Celtec was machined as well as the temperature range of the environment in which the Celtec is installed.

In a location with a relatively constant temperature and lack of direct sunlight, such as an indoor display stand, any thermal expansion and contraction of the Celtec material will usually be insignificant.

If, however, a finished Celtec project will be used in a setting that has noticeable fluctuations in temperature, the potential expansion and contraction should be considered when producing the part(s). Expansion of the Celtec material occurs when it is placed in an environment with higher temperatures than the temperature at which it was originally cut. Conversely, contraction, or shrinkage, of the material takes place when it is in a colder environment than that in which it was cut.

**NOTE!**

Calculations for thermal expansion and contraction should be made for both the width and the length of the Celtec material.

Celtec should not be used in areas that exceed 140°F, at which temperature the Celtec will soften and change dimensions permanently. **Dark colors are generally not recommended for outdoor use, as they absorb heat energy and can easily exceed the maximum allowable temperature of 140°F.**

**NOTE!**

When exposed to direct sunlight, white Celtec will generally show a surface temperature 10°F to 20°F higher than the actual air temperature.



# FASTENING

CELTEC®

## Celtec Thermal Expansion/Contraction Worksheet

The following worksheet will help calculate the correct size to cut a Celtec part in order to allow for potential expansion and contraction after installation.

Expansion:	
1. Highest expected temperature in the environment in which the Celtec part will be used (in degrees Fahrenheit)	F°
2. Approximate temperature of the Celtec part at the time it was cut (in degrees Fahrenheit)	F°
3. Total temperature difference (subtract line 2 from line 1)	F°
4. Total length of Celtec part (in inches)	in.
5. Total amount of expansion (line 3 x line 4 x 0.00004)	in.

Contraction	
1. Approximate temperature of the Celtec part at the time it was cut (in degrees Fahrenheit)	F°
2. Lowest expected temperature in the environment in which the Celtec will be used (in degrees Fahrenheit)	F°
3. Total temperature difference (subtract line 2 from line 1)	F°
4. Total length of Celtec part (in inches)	in.
5. Total amount of contraction (line 3 x line 4 x 0.00004)	in.

### Conversion Table: Decimal to Fractional Inches

0.032" = 1/32"	0.156" = 5/32"	0.281" = 9/32"	0.406" = 13/32"
0.062" = 1/16"	0.187" = 3/16"	0.312" = 5/16"	0.437" = 7/16"
0.093" = 3/32"	0.218" = 7/32"	0.343" = 11/32"	0.468" = 15/32"
0.125" = 1/8"	0.250" = 1/4"	0.375" = 3/8"	0.500" = 1/2"

**Celtec Thermal Expansion/Contraction Worksheet Example:**

A Celtec part is cut in a shop where the temperature is 70°F. The part is 96" long. The part will be installed as part of an outdoor sign on a concrete building. The highest expected temperature after installation is 100°F, and the lowest expected temperature is 10°F.

<b>Expansion:</b>	
1. Highest expected temperature in the environment in which the Celtec part will be used (in degrees Fahrenheit)	100 F°
2. Approximate temperature of the Celtec part at the time it was cut (in degrees Fahrenheit)	70 F°
3. Total temperature difference (subtract line 2 from line 1)	30 F°
4. Total length of Celtec part (in inches)	96 in.
5. Total amount of expansion (line 3 x line 4 x 0.00004)	0.1152 in.

<b>Contraction</b>	
1. Approximate temperature of the Celtec part at the time it was cut (in degrees Fahrenheit)	70 F°
2. Lowest expected temperature in the environment in which the Celtec will be used (in degrees Fahrenheit)	10 F°
3. Total temperature difference (subtract line 2 from line 1)	60 F°
4. Total length of Celtec part (in inches)	96 in.
5. Total amount of contraction (line 3 x line 4 x 0.00004)	0.2304 in.

Using the worksheet and converting the results to fractional inches, the maximum amount of expansion of the 96" part will be approximately 1/8", and the minimum amount of contraction will be approximately 1/4". To allow for this expansion and contraction, the Celtec sign should not be fastened directly to the concrete exterior wall, as it might then buckle, crack, or warp during temperature fluctuations. In this example, slots for fasteners or U-channel tracking should be cut to allow the part to expand up to 96 and 1/8" and contract to 95 and 3/4".

# FASTENING

CELTEC®

Celtec Linear Expansion/Contraction Quick Reference:				
Total Temperature Change (+/-)	Expansion/Contraction of Material at Standard Lengths/Widths (in inches)			
	48 inches	60 inches	96 inches	120 inches
20°F	0.038"	0.048"	0.076"	0.096"
40°F	0.076"	0.096"	0.153"	0.192"
60°F	0.115"	0.144"	0.230"	0.288"
80°F	0.153"	0.192"	0.307"	0.384"
100°F	0.192"	0.240"	0.384"	0.480"
120°F	0.230"	0.288"	0.460"	0.576"
140°F	0.268"	0.336"	0.537"	0.672"

## Screwing and Nailing

Any type of screw or nail can be used to fasten Celtec material: pre-drilling is typically unnecessary. Power nailers and screw-driving equipment are suggested. Inserting the screw or nail in an elongated slot or an oversized hole is recommended so that the material can expand or contract if fluctuations in temperature occur (Figure 2b). For best results, use oversized washers or grommets in combination with screws.

Screws should be tightened and then retightened slightly to allow the Celtec material to expand or contract as necessary.

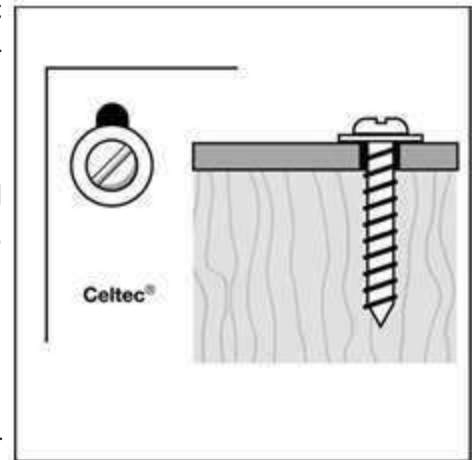


Figure 2b

In small panels under 18" or in temperature-controlled environments, allowing for expansion and contraction is not mandatory. Mechanical failures in heating or cooling systems and other unexpected factors can, however, affect temperatures radically and may cause unanticipated expansion or contractions.

Nailing is suggested for small, thin panels of Celtec material. To use larger nails and screws, holes should be placed at least one inch from any edges and predrilled (Figure 2c). Celtec is more brittle in colder temperatures, so if work is being completed outdoors in low temperatures, be careful to avoid possible fracturing of the Celtec material.

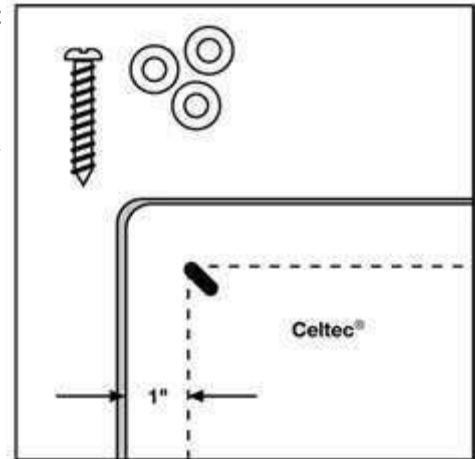


Figure 2c

## Installation

Celtec is manufactured as an extruded PVC product with a directional grain running the entire length of the sheet. This manufacturing process gives Celtec greater flexural strength in the direction of the extrusion. Because of this characteristic, flag-type signs should be cut so that the grain direction is horizontal to the anchor point (Figure 2d). This precaution permits the Celtec material to flex and withstand wind pressure.

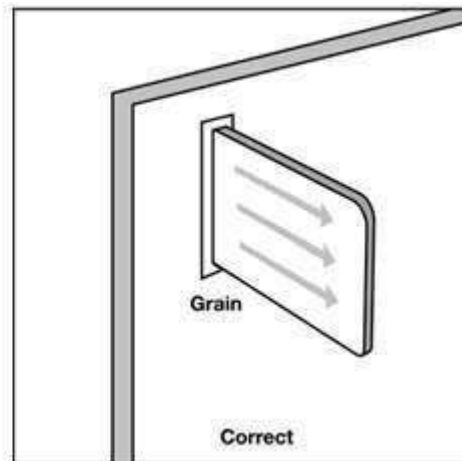
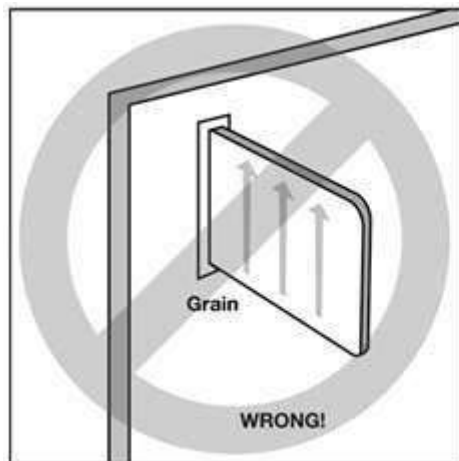


Figure 2d

### NOTE!

Failure to cut and attach the material in the proper direction may cause fracturing to occur, particularly in narrow signs.

# FASTENING

CELTEC®

## Bonding and Adhesives

### Celtec to Celtec or other PVC material

For bonding Celtec to itself or another PVC material, a solvent-based adhesive system used for rigid, non-expanded PVC will provide the best results. Solvent-based adhesives are sold through various suppliers. Proper ventilation and a clean working environment are essential for this type of bonding.

#### NOTE!

When bonding large panels face to face, avoid using solvent-based adhesives, which will not cure properly.

### Celtec to various substrates

There are numerous types of adhesives that can be used with specific substrates. Contact, epoxy, rubber-based, and urethane adhesive systems are all acceptable. For best results, test the selected adhesive for suitability in a particular application before use.

Parts to be joined should fit without forcing and be prepared with the appropriate cleaner. Depending on the type of application and the consistency of the adhesive, the adhesive can be applied to the material with a brush, a syringe, or an eyedropper. If cement is applied to one surface, let the two surfaces be in gentle contact for a few seconds to allow the cement to soften the dry surface, then press the parts together in firm contact (Figure 2e).

Figure 2e



#### NOTE!

When using any adhesive system, be certain to follow the manufacturer's storage and handling recommendations. Disposing of spent adhesives or solvents may be subject to local regulations.

# FASTENING

CELTEC®

## Adhesives and Manufacturers

The following tables list several adhesives and their bonding applications for materials commonly used in fabricating Celtec products.

The second table contains contact information for the manufacturers of those products. Additional adhesive manufacturers are listed in the third table.

The listed adhesives and manufacturers are for informational purposes only. Please perform the appropriate tests to ensure that the materials will produce the desired results.

Celtec Recommended Adhesives and Applications										
Manufacturer	Adhesive	Celtec To:								
		Celtec	Rubber	Glass	Aluminum	Metal	Masonry	Other Plastics	Wood	High Pressure
3M Adhesive Division	3M Scotch-Weld 2216B/A, 3549 B/A (structural bond)	X	X			X	X	X	X	
	3M Scotch-Grip 4475, Fast Bond 30 Neutral (nonstructural bond)								X	
	Fast Bond 30-NFGreen Contact Adhesive	X		X				X	X	X
Daubert Chemical Co.	Daubond 8050	X			X	X		X	X	
	Daubond 8855	X				X		X	X	
Dow Corning Corp.	832	X						X		
E-Z Weld	E-Z Weld	X								
GE Silicones	Silicone II Window and Door	X		X	X	X		X	X	
Gorilla Glue	Gorilla Glue	X		X	X	X	X	X	X	
	Gorilla Super Glue	X	X		X	X		X	X	
	Gorilla Epoxy	X		X	X	X	X	X	X	
Henkel Loctite Corp.	Prism 454 Surface Instant Gel	X				X		X	X	
	Speedbonder 324, 325, 326 (structural bond)	X						X		
Oatey Co.	PVC and ABS and CPVC All Purpose Cement	X						X		
Sashco	Lexel	X		X	X	X		X	X	
Satellite City	Hot Stuff Super T, Special T	X						X	X	
Schwartz Chemical Co.	VC1, VC2	X								
	Rez-n-Bond			X	X	X		X	X	
TEC Specialty Products	749	X		X	X	X		X	X	

# FASTENING

CELTEC®

## Recommended Adhesive Manufacturers

Company	Contact	Address
3M Adhesives <a href="http://www.3m.com">www.3m.com</a>	800.362.3550 F: 651.733.9175	3M Corporate Headquarters / 3M Center St. Paul, MN 55144
E-Z Weld Inc. <a href="http://www.e-zweld.com">www.e-zweld.com</a>	561.844.0241 F: 561.848.8950	1661 Old Dixie Highway Riviera Beach, FL 33404
Daubert Chemical Co. <a href="http://www.daubertchemical.com">www.daubertchemical.com</a>	800-688-0459 F: 708.496.7367	4700 S. Central Avenue Chicago, IL 60638
GE Silicones Inc. <a href="http://www.siliconeforbuilding.com">www.siliconeforbuilding.com</a>	877.943.7325	9930 Kinsey Avenue Huntersville, NC 28078
Henkel Loctite Corp. <a href="http://www.loctite.com">www.loctite.com</a>	800-624-7767 F: 847.648.9819	Contact local dealers
Oatey Company <a href="http://www.oatey.com">www.oatey.com</a>	800.321.9532 F: 216.267.6538	4700 West 160th Street Cleveland, OH 44135
Sashco <a href="http://www.sashco.com">www.sashco.com</a>	800-767-5656 F: 303.286.0400	10300 107th Place Brighton, CO 80601
Satellite City <a href="http://www.caglu.com">www.caglu.com</a>	800.786.0062 F: 888.200.9413	3543 Old Conejo Road, STE 101 Newbury Park, CA 91320
Schwartz Chemical Company <a href="http://www.schwartzchem.com">www.schwartzchem.com</a>	905.683.0411 F: 905.428.2057	777 McKay Road Pickering, Ontario, Canada L1W 3A3

## Additional Adhesive Manufacturers

Company	Contact	Address
Bostik Findley, Inc. <a href="http://www.bostik.com">www.bostik.com</a>	414.774.2250	11320 Watertown Plank Road Wauwatosa, WI 53226
IPS <a href="http://www.ipscorp.com">www.ipscorp.com</a>	310-898-3300 F: 901.853.5008	455 W. Victoria Street Compton, CA 90220
Liquid Nails <a href="http://www.liquidnails.com">www.liquidnails.com</a>	800.634.0015	15885 West Sprague Road Strongsville, OH 44136
Parabond <a href="http://www.parabond.com">www.parabond.com</a>	800-552-6225	1105 S Frontenac St Aurora, IL 60504
TACC <a href="http://www.itwtacc.com">www.itwtacc.com</a>	800.503.6991 F: 800.231.8222	56 Air Station Industrial Part Rockland, MA 02370



## Additional Manufacturers continued

Company	Contact	Address
Grizzly Glue <a href="http://www.grizzlyglue.com">www.grizzlyglue.com</a>	800.779.3935	10751 N. Territorial Dexter, MI 48130
OSI Sealants, Inc. <a href="http://www.osipro.com">www.osipro.com</a>	800.624.7767	One Henkel Way, Rocky Hill, Ct 06067
Siroflex, Inc. <a href="http://www.siroflexinc.com">www.siroflexinc.com</a>	800.359.6389 F: 864.458.9092	1320 Garlington Road Greenville, SC 29615
White Lightning (KPG) <a href="http://www.wlcaulk.com">www.wlcaulk.com</a>	800-241-5295 F: 800-380-9422	101 Prospect Avenue Cleveland, OH 44115

# FORMING/WELDING

CELTEC®

## 3

Celtec can easily be shaped using conventional methods, such as heat bending, pressure forming, and vacuum forming. Because Celtec heats and cools very quickly, it creates rapid cycle times that reduce labor, making the material excellent for sign faces and point-of-purchase displays.

### Heat Bending

Celtec sheet material can be bent by using Calrods, radiant heaters, strip heaters (Figure 3a) or air-circulated ovens. Heat guns can also be used on small areas. To ensure best results, a rheostat should be used to control heating of the Celtec so that the surface temperature does not exceed 340°F.

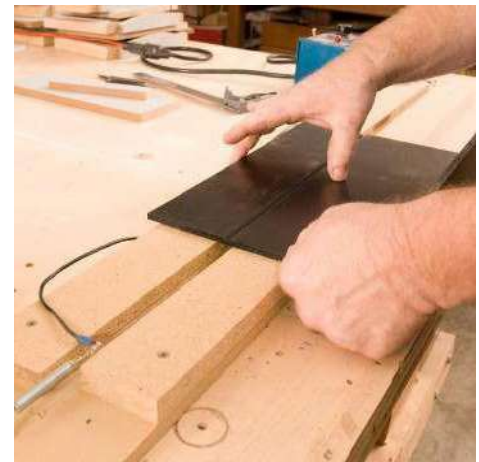


Figure 3a

When using a metal contact strip heater, cover the heater strip with Teflon spray to prevent marking the Celtec. Different sizes of rectangular heating bars can be used to produce bends of different radii. The larger the heated area of the Celtec, the larger the radius that can be created.

Celtec should be heated from both sides when the sheet is thicker than 4mm. Celtec heats much more quickly than solid PVCs or acrylics and requires heating at the rate of approximately 30 to 40 seconds per millimeter of thickness prior to bending.

#### NOTE!

Heating Celtec material over 340°F can cause the surface to become rough and possibly discolor.

To form tighter bends with smaller radii, use a smaller heated area on the upper surface (inside the bend) of the Celtec sheet and a larger heated area on the bottom surface (on the outside of the bend) of the sheet. A minimum radius of twice the sheet thickness is necessary to avoid breakage (Figure 3b). When bending the Celtec into an angle, typically the extension of the Celtec on either side of the angle should be at least 2 times the thickness, when the entire sheet is heated.

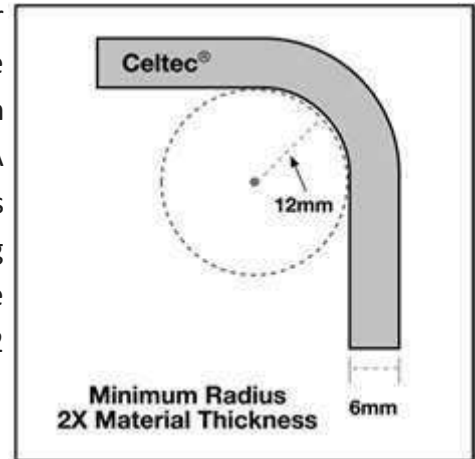


Figure 3b

Once Celtec is bent, place it in a fixture, such as a jig or clamp, to cool. Fans and/or compressed air can be used to speed the cooling process.

## Pressure or Drape Forming

Celtec can be heated using radian heat panes or air-circulating ovens. Either male or female molds can be coupled with plug assists or forced air to form parts (Figure 3c). This procedure is recommended for simple shallow forms with low definition. Conventional equipment used for thermoplastics is also ideally suited for Celtec.

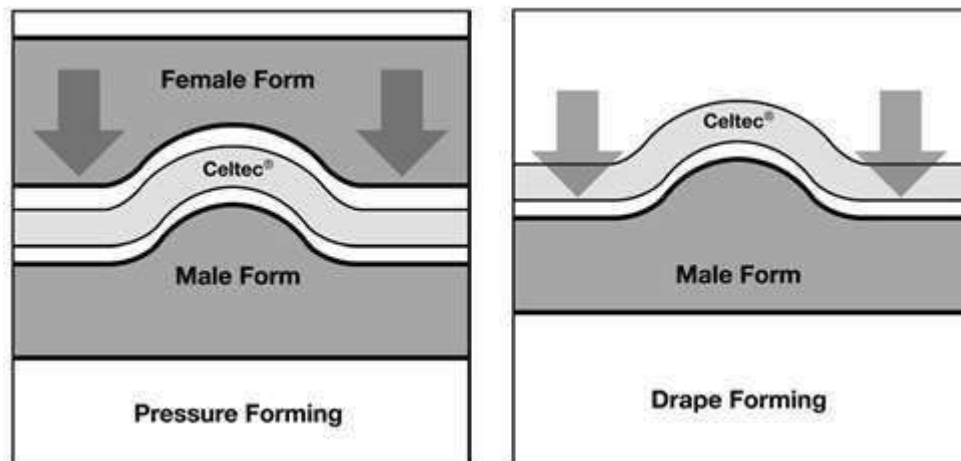


Figure 3c

# FORMING/WELDING

CELTEC®

**NOTE!**

When using radiant heaters, be careful not to overheat the surface.

If the Celtec material is over 4mm thick, both sides of the sheet should be heated (Figure 3d). When heating from only one side, the top heater should be set at 750°F or below. With two-sided heating, the top heater should be at 750°F and the bottom heater at 650°F. If using an air-circulated oven, the temperature should be between 260°F and 280°F.

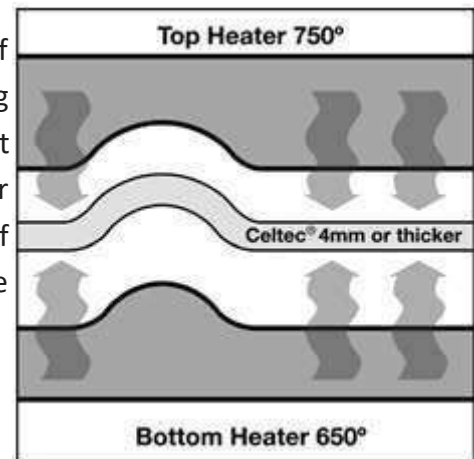


Figure 3d

After the Celtec is heated, place it immediately into the mold. The male mold should have a draft angle of at least 5°. Depending upon the part to be formed, the Celtec material may need to be larger than the mold to allow for shrinkage and/or clamping.

Because there are limits to the Celtec material's ability to stretch while still producing aesthetically acceptable results, the depth of the part that can be successfully created will depend upon both the mold and the part's design.

Cycle times for Celtec are very fast, approximately 15 to 20 seconds per millimeter of thickness with radiant heaters and 30 to 40 seconds per millimeter in air-circulating ovens.

**NOTE!**

When creating or selecting a mold for Celtec material, it is important to use a mold without sharp corners.

## Vacuum Forming

Vacuum forming of Celtec is similar to pressure forming except that it is generally used when greater part detail and dimensional repeatability are necessary (Figure 3e). The forming temperature for Celtec is also higher, generally 300°F to 340°F. Exceeding 340°F is not recommended because it can cause bubbling of the Celtec surface.

Molds for vacuum forming are generally made of wood or plaster for short-life short runs and of nonferrous metals for long-life long runs. For metals, aluminum is generally the material of choice. Molds

should be designed with radii at least two times the material thickness and draft angles of 5° or greater. Vacuum holes should not exceed 1/32" in diameter.

Figure 3e



## Heat Welding

Celtec can be joined using fusion welding, ultrasonic welding, and hot gas welding.

For Celtec thickness over 6mm, butt fusion welding is recommended. In general, the pressure used for solid PVC must be reduced for expanded PVC. Exact recommendations are dependent on the length and thickness of the Celtec part to be welded. For more precise information, contact Wegener North America.

Ultrasonic welding technology is based on the principal of converting electrical energy into mechanical energy for the purpose of changing the physical, chemical, or biological properties of materials or systems. Key benefits of HPU (High Power Ultrasonic) include friction reduction, solid state bonding, extremely fast cycle times, and real-time feedback. For more information contact, Edison Welding Institute and Wegener Welding:

**Edison Welding Institute**  
**1250 Author E. Adams Drive**  
**Columbus, OH 43221**  
**614.688.5000**  
[www.ewi.org](http://www.ewi.org)

**Wegener Welding**  
**16W301 S. Frontage Road**  
**Burr Ridge, Illinois 60527**  
**630.789.0990**  
[www.wegenerwelding.com](http://www.wegenerwelding.com)

# FORMING/WELDING

Hot gas welding can be performed with a hot air gun and welding rod (Figure 3f). The air should be clean and free of all contaminants. If the air is not clean, an inert gas such as nitrogen can be used. The welding temperature and volume of air should be adjustable. Celtec welds ideally with a Type II welding rod but can also be welded with a Type I welding rod. The weld strength is approximately 60% of the base material.

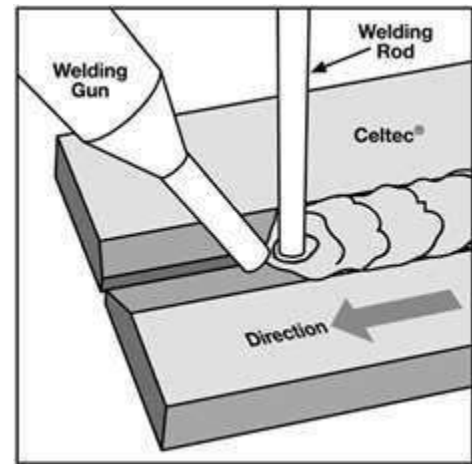


Figure 3f

The Celtec sheets to be welded should be free from dust or oil. For butt welding using the hot gas method, sheets should be chamfered using a table saw, milling machine, or router. The angle should be 60° for round bends and 80° for triangle bends with corner welds at right angles (Figure 3g). The chamfer should be at 45°.

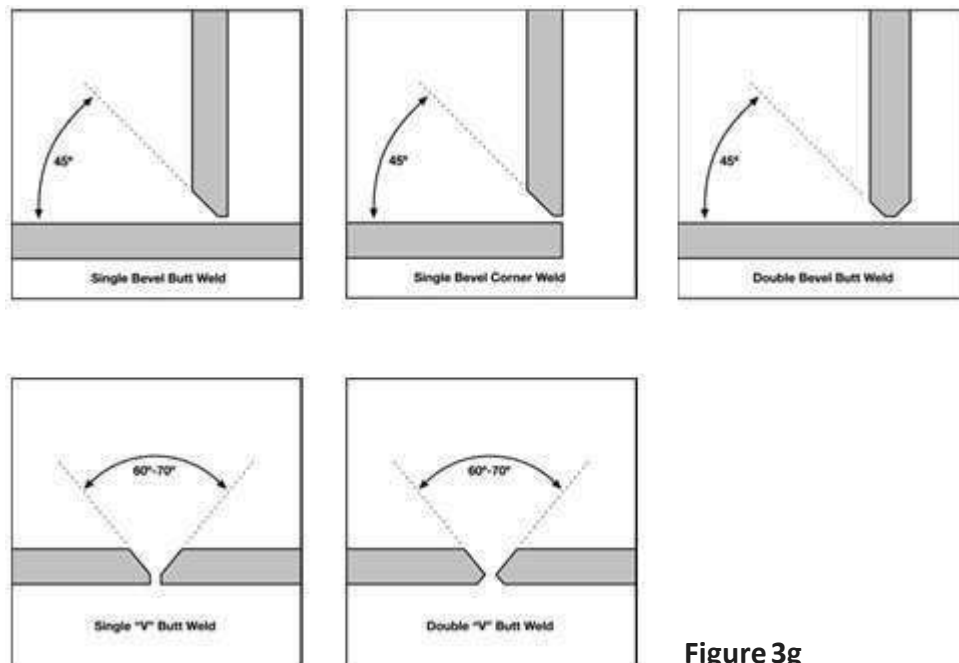


Figure 3g

To weld Celtec material, feed the rod through the gun and apply pressure on the rod as the sheet and rod are heated simultaneously. The temperature of the gas should be at 680°F when measured 3/16" inside the tip of the gun. The volume of air should be 50 liters per minute using a flow regulator with welding pressure at approximately 2 to 3.5 lbs., depending on the rod diameter. Following these guidelines, welding speeds between 11 to 20 inches per minute are possible.

<b>NOTE!</b>	Skiving off the weld joint for aesthetic purposes will reduce weld strength.
--------------	--

## Manufacturers

### Bending and Forming Equipment

Company	Contact	Address
C.R. Clarke & Co., Inc. <a href="http://www.crclarke.co.uk">www.crclarke.co.uk</a>	800.676.7133 F: 407.566.0756	1272 Aquila Loop Kissimmee, FL 34747
Kamweld Technologies, Inc. <a href="http://www.kamweld.com">www.kamweld.com</a>	617-558-7500 F: 781.762.0052	90 Access Road Norwood, MA 02062
Wegener North America, Inc. <a href="http://www.wegenerwelding.com">www.wegenerwelding.com</a>	630.489.0990 F: 630.789.1380	16W301 S. Frontage Road Burr Ridge, IL 60527

### Thermoforming Equipment

Company	Contact	Address
Brown Machine LLC <a href="http://www.brown-machine.com">www.brown-machine.com</a>	989.435.7741 F: 989.435.2821	330 North Ross Street Beaverton, MI 48612
Lamco Machine Tool Inc. <a href="http://www.lamcomachine.com">www.lamcomachine.com</a>	252.247.4360 F: 252.247.4633	135 Industrial Drive Morehead City, NC 28557
MAAC Machinery Corporation <a href="http://www.maacmachinery.com">www.maacmachinery.com</a>	800.558.6222	590 Tower Boulevard Carol Stream, IL 60188

# FORMING / WELDING

CELTEC®

## Line Bending Equipment

Company	Contact	Address
Big Chief Supply Company www.gobigchief.com	513-271-7411 F: 513 271 0790	5150 Big Chief Drive Cincinnati, OH 45227
Craftics Inc www.craftics.net	505-338-0005 F: 505-338-0008	3615 High Street NE Albuquerque, NM 87107
FTM Inc www.fabricatorstoolsandmaterials.com	530-626-1986 F: 505-642-2602	327 Industrial Drive, Unit 1 Placerville, CA 95667
Kamweld Industries www.kamweld.com	616-558-7500	100 Access Rd Norwood, MA 02062
Waltow www.waltow.com	800-928-5692	5514 Meadow Pine Ct Orlando FL 32819

## Welding Equipment

Company	Contact	Address
Laramy Products www.laramyplasticwelders.com	802-626-9328 802-626-5529	40 Sandy Lane Lyndon, VT 05851
Kamweld Industries www.kamweld.com	616-558-7500	100 Access Rd Norwood, MA 02062
FTM Inc www.fabricatorstoolsandmaterials.com	530-626-1986 F: 505-642-2602	327 Industrial Drive, Unit 1 Placerville, CA 95667
Wegener Welding www.wegenerwelding.com	630-789-0990 F: 630-789-1380	16W301 S. Frontage Rd Burr Ridge IL 60527

## Ultrasonic Equipment

Company	Contact	Address
Dukane www.dukane.com	630-797-4900	2900 Dukane Drive St Charles, IL 60174
Hermann Ultrasonics www.hermannultrasonics.com	630-626-1626 F: 630-626-1627	1261 Hardt Circle Bartlett, IL 60103
Sonobond Ultrasonics www.sonobondultrasonics.com	800-323-1269 F: 610-692-0674	1191 McDermott Dr West Chester, PA 19380



[This page intentionally left blank.]

# GRAPHIC APPLICATIONS

CELTEC®

## 4

Celtec performs outstandingly in a wide range of graphic applications, including those involving paints, screen printing, digital flatbed printing, and vinyl films. Celtec can be used to create weather-resistant signs, displays, or point-of-purchase (POP) materials. The smooth Celtec surface is ideal for all types of graphics, and it requires little surface preparation or surface treatment.

### General Considerations

To ensure best results for any graphic applications using Celtec, consider the following factors that may affect the finished installation:

- Environmental and safety concerns
- Weathering
- Chemical resistance
- Ease of application
- Cost-effectiveness
- Hardness
- Scratch resistance
- Priming or multicoated paint applications.

### Cleaning/Pretreating

Before screen printing or painting Celtec, the surface area should be cleaned with isopropyl alcohol and a clean white cloth. Depending on the specific application, certain pretreatments may also be required, as described in the following sections.

#### TIP

Because of the wide range of products available, select paints carefully for each application. Initial testing of the selected paint system is recommended before a product run.

## Digital Flatbed Printing

Digital ink jet printing has grown in popularity for printing signs, POP displays, exhibits, point-of-sale signs, etc. The technology has advanced very rapidly to increase printing speeds, offer higher DPI, offer white ink technology for dark substrates, and reduce the capital investment required to buy a machine.

Since Celtec is a rigid substrate, it requires a flatbed feed system. Most of today's equipment manufacturers offer machines that can print materials up to 2" thick (Figure 4a). Digital printing allows shorter production runs compared to screen printing. Customers who have digital flatbed printers can print directly from a PC to the substrate, which eliminates costly setup.



Figure 4a

### Standard Celtec is ideal for flatbed printing for the following reasons:

- Direct printing to Celtec eliminates the mounting and laminating steps necessary when printing to paper.
- Celtec can be used with UV curing machines or screen print solvent systems. Always check with the manufacturer before printing for compatible solvent-based ink systems.
- Celtec has the best whiteness for reproducing choice colors.

## Digital Printing Equipment

Most of the machines today use UV curing inks, although there are some that use solvent systems. Most equipment companies have proprietary inks that are used with their equipment, and it is therefore impossible to cover all combinations. See the table at the end of the chapter for a list of equipment that has run Celtec at the equipment's manufacturing site or is used in the field by our customer base.

.

# GRAPHIC APPLICATIONS

CELTEC®

## Printing

Celtec provides an excellent surface for screen printing and accepts a wide range of inks (Figure 4b). When silk-screening on Celtec, crisp, full coverage is achieved with printing inks that normally would be used for other rigid PVC products.

For best results when screen printing, be sure that the Celtec sheet has been degreased and cleaned with a lint-free cloth. Always use PVC screen inks and thinners from the same product line and manufacturer. Incompatibility of inks and thinners may cause poor print quality, surface cracking, and reduce the life span of the Celtec material.



Figure 4b

### TIP

Celtec in the 10MM thickness and above provides an extremely smooth surface for printing.

## Painting/Varnishing

Although Celtec requires no painting, any painting planned for a project should be completed as soon as possible, either during or soon after the construction process. Priming is not mandatory but should be performed prior to painting if the paint manufacturer's warranty is a consideration. To avoid heat buildup, light paint colors are recommended for most applications. Sheets of 19mm and greater thickness can accept slightly darker colors, but not very dark (i.e., black, brown, forest green, etc.).

Paint adheres to Celtec material exceptionally well. In general, no primers are needed to prepare the Celtec sheet for painting, although the surface of the Celtec should be dry, clean, and degreased for best results. Any method of paint application may be used, including power or manual rollers, spray, guns, conventional brushes, sponge-type brushes, artists' lettering brushes, and/or dipping.

### TIP

A sample of Celtec should be flood-screened prior to production to ensure a finished product of acceptable quality.

Apply paint in only one direction if using a brush. Celtec material generally requires only one coat of paint to finish.

**NOTE!**

Most enamels and lacquers systems are generally not recommended for Celtec.

Celtec is a thermoplastic material that will deform at temperatures above 140°F and thus cannot be heat dried at high temperatures. Air dry paints are therefore most successful with Celtec material.

**Surface Preparation**

Before painting or printing, clean the surface of the Celtec material with a clean cloth and an aliphatic solvent, such as isopropyl or denatured alcohol, heptane, octane, UM&P, or naphtha, to produce good adhesion.



Figure 4c

**NOTE!**

Remove any scratches on the Celtec material's surface by sanding with a fine sandpaper or by rapidly fanning the area with a heat gun. Once sanded, the original finish is removed.

# GRAPHIC APPLICATIONS

CELTEC®

## Cross-Hatch Adhesion Test

Good paint and ink adhesion is critical to achieving a successful finished product. The cross-hatch adhesion test described below should be performed on every paint or ink system unless it is specifically not recommended for Celtec material. For paint and ink brands, consult the list of recommended manufacturers at the end of this chapter.

### NOTE!

Although most paints will feel dry to the touch after 24 hours, some paints may not achieve full adhesion to the Celtec material for two to three weeks after application.

1. On a sheet of Celtec, apply the paint to be tested for adhesion. Let dry for a minimum of 48 hours.
2. Using a knife with a replaceable blade, make 11 parallel cuts  $\frac{1}{16}$ " apart. At a 90° angle to the first set of 11 cuts and crossing them, make a second set of 11 parallel cuts, also  $\frac{1}{16}$ " apart (Figure 4d). The purpose of the cuts is to break the film plane of the paint.
3. Pressing firmly, apply a  $\frac{1}{2}$ "-wide strip of strong tape (i.e., Scotch™ brand) across the scored area (Figure 4e).

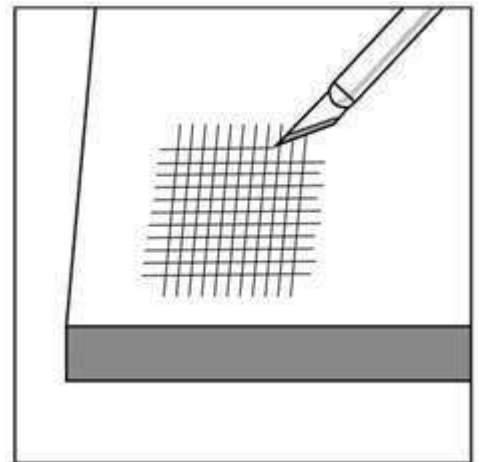


Figure 4d

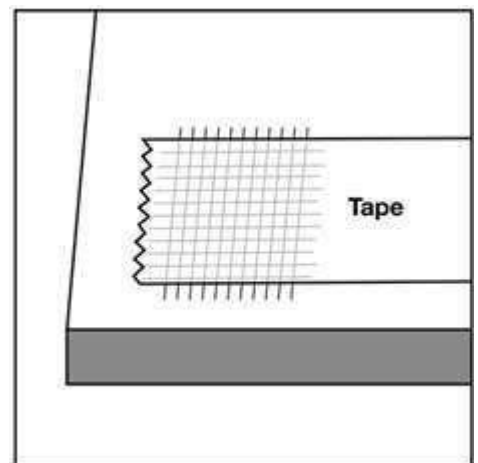


Figure 4e

4. Immediately and in one rapid motion, remove the tape by pulling it back at a 180° angle, parallel to the Celtec sheet (Figure 4f).

5. Proper adhesion has been obtained if paint remains on the Celtec after the tape is removed. Relative paint adhesion comparisons can also be made by inspecting the amount of paint remaining in the area that was covered by the tape.

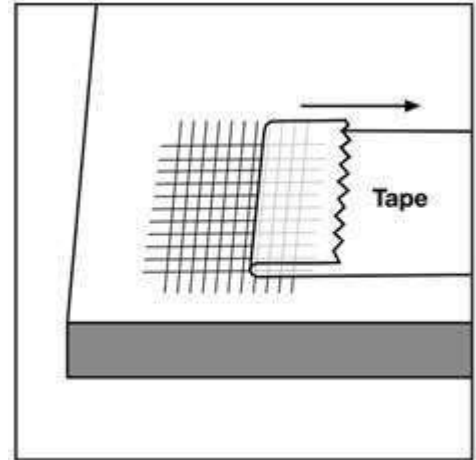


Figure 4f

## Application

Concentrated forms of paints and ink should be thinned before use. Follow the manufacturer's guide and recommendations.

For best results, conventional air-spraying equipment can be used on Celtec material (Figure 4g). Paints may also be applied with a paint brush or roller.

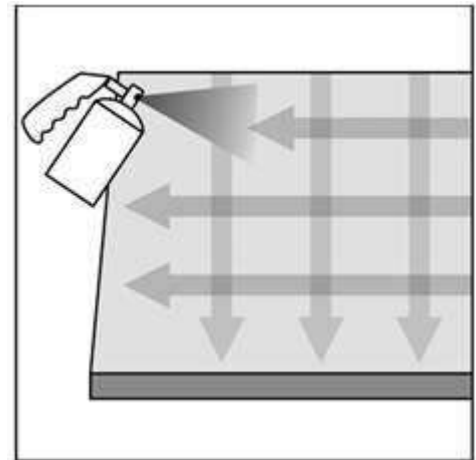


Figure 4g

## Spraying Hints

- Do not use airless spraying equipment. Air-operated equipment, such as DeVilbiss spray finishers, is preferred.
- Use a spray nozzle with a #30 air cap to disperse the paint properly.
- Set the air pressure on the material at 24 psi and 40-50 psi on the air cap.
- Keep the spray gun nozzle perpendicular to the surface of the material
- Make three spraying passes in one direction, turn the panel 90°, and make three additional passes.
- Lightly sand any runs that occur on the edges of the Celtec with 200 grit sandpaper and touch up with additional paint as needed.

# GRAPHIC APPLICATIONS

CELTEC®

## Vinyl Lettering

When applying text to Celtec, pressure-sensitive or static-cling vinyl letters are highly recommended. As with other graphic applications, the surface of the Celtec material must be free of dust or other small particles, degreased, and dry before applying lettering (Figure 4h).



Figure 4h

## Vinyl Graphics Manufacturers

Company	Contact	Address
3M Commercial Graphics <a href="http://www.3m.com">www.3m.com</a>	800.328.3908	3M Center, Building 0220-12-E-04 St. Paul, MN 55144
Arlon <a href="http://www.arlon.com">www.arlon.com</a>	714.540.2811 F: 800.329.2756	2811 S. Harbor Boulevard Santa Ana, CA 92704
Avery Dennison <a href="http://www.averydennison.com">www.averydennison.com</a>	440-534-6000	8080 Norton Parkway Mentor, OH 44060
Kapco Graphics <a href="http://www.kapco.com">www.kapco.com</a>	330.678.1626 F: 330.678.3922	1000 Cherry Street Kent, OH 44240
ORACAL USA <a href="http://www.oracal.com">www.oracal.com</a>	914.851.5000 F: 914.851.5050	1100 Oracal Parkway Black Creek, GA 31308



## Manufacturers

### Flatbed Printer Manufacturers

Company	Contact	Address
Agfa Graphics <a href="http://www.agfagraphics.com">www.agfagraphics.com</a>	800.540.2432 F: 201.440.6794	611 River Drive, Center 3 Elmwood Park, NJ 04704
Canon Solutions America <a href="http://www.csa.canon.com">www.csa.canon.com</a>	844-443-4636	One Canon Park Melville, NY 11747
CET Color <a href="http://www.cetcolor.com">www.cetcolor.com</a>	404-228-1259	4450 Commerce Drive SW Atlanta, GA 30336
Durst Image Technology <a href="http://www.durstus.com">www.durstus.com</a>	650-357-3500 F: 585.486.0350	50 Methodist Hill Drive, Suite 100 Rochester, NY 14623
Epson America <a href="http://www.epson.com/usa">www.epson.com/usa</a>	800-463-7766	3131 Katella Avenue Los Alamitos, CA 90720
EFI - Inkjet Solutions <a href="http://www.efi.com">www.efi.com</a>	650-357-3500 F: 650-357-3907	6453 Kaiser Dr Fremont CA 94555
FUJIFILM North America <a href="http://www.fujifilmgraphics.com">www.fujifilmgraphics.com</a>	914-789-8100	200 Summit Lake Drive Valhalla, NY 10595
Hewlett Packard <a href="http://www.hp.com">www.hp.com</a>	800.752.0900	300 Hanover Street Palo Alto, CA 94304
Mimaki USA <a href="http://www.mimakiusa.com">www.mimakiusa.com</a>	888.530.4021	150 Satellite Boulevard NE, Suite A Suwanee, GA 30024
Ricoh Americas <a href="http://www.ricoh-usa.com">www.ricoh-usa.com</a>	610-296-8000	300 Eagleview Blvd. Exton, PA 19341
Roland DGA <a href="http://www.rolanddga.com">www.rolanddga.com</a>	949-727-2100	15363 Barranca Parkway Irvine, CA 92618

# GRAPHIC APPLICATIONS

CELTEC®

## Manufacturers

### Primer Manufacturers

Company	Contact	Address
KILZ <a href="http://www.kilz.com">www.kilz.com</a>	714-545-7101	1801 E St Andrew Place Sanata Ana, CA 92705
One Shot, LLC <a href="http://www.1shot.com">www.1shot.com</a>	773.646.2778	1701 East 122nd Street Chicago, IL 60633
Ronan Paints <a href="http://www.ronanpaints.com">www.ronanpaints.com</a>	800-307-7951 F: 718.282.0406	89 Taft Ave Newburgh, NY 12550

### Paint Manufacturers

Company	Contact	Address
Matthews Paint (PPG) <a href="http://www.matthewspaint.com">www.matthewspaint.com</a>	800-323-6593	One PPG Place Pittsburgh, PA 15272
One Shot <a href="http://www.1shot.com">www.1shot.com</a>	773-646-2778	1701 East 122 <sup>nd</sup> Street Chicago, IL 60633
Sherwin Williams <a href="http://www.sherwin-williams.com">www.sherwin-williams.com</a>	800-474-3794	Contact local dealers
Benjamin Moore <a href="http://www.benjaminmoore.com">www.benjaminmoore.com</a>	866.708.9181	100 Paragon Dr Montvale, NJ 07645
Blue River Coatings <a href="http://www.bluerivercoatings.com">www.bluerivercoatings.com</a>	402-436-3962 F: 402-463-4476	2910 S. Nebraska Ave Hastings, NE 68901

## Silkscreen Ink Manufacturers

Company	Contact	Address
FujiFilm <a href="http://www.fujifilm.com">www.fujifilm.com</a>	603-443-5300	109 Etna Rd Lebanon, NH 03766
Sun Chemical Corp <a href="http://www.sunchemical.com">www.sunchemical.com</a>	973-404-6000	35 Waterview Blvd Parsippany, NJ 07054
NazDar <a href="http://www.nazdar.com">www.nazdar.com</a>	913-422-1888 F: 913-422-2295	8501 Hedge Ln Terrace Shawnee, KS 66227

# SPECIAL APPLICATIONS

CELTEC®

## 5

Celtec's light weight, strength, and versatility allow it to be used in many special applications. Celtec is an effective core material for panel constructions using common synthetic resins or a wide variety of structural adhesives or plastics. Celtec's smooth surface and adherence capacity make it an excellent choice for photo-mounting and laminating, whether by hand for small jobs or with automated equipment for larger production runs.

### Photo-Mounting

Celtec offers an excellent surface for mounting numerous materials, including Cibachrome prints, lithographs, blueprints, tissues, and nearly all types of other papers (Figure 5a). Due to its strength and rigidity, Celtec produces a stronger finished product compared to other available substrate materials.

For example, the corners of Celtec photo-mounting application will not bend or crease, as wall items mounted on cardboard or foam-type materials will.

One significant advantage of photo-mounting is Celtec's smooth finish relative to other thermoplastics. This finish allows prints to be easily repositioned or other mounted materials to be removed when necessary.

Once the mounting process is complete, Celtec can be laminated and then routed, heat bent, drilled, silk screened, or painted for use in virtually any display application.

The preferred methods of photo-mounting on Celtec sheets are:

- Cold mounting using cold roller laminators, such as Warman-Greig, Greig or Sealeze presses.
- Cold vacuum mounting with VacuSEAL presses.
- Hand laminating.

Figure 5a



The sophisticated Greig press is used by large photo labs, while the Sealeze press is more commonly found at small commercial labs. The VacuSEAL press is utilized primarily by photo shops.

**NOTE!**

Because Celtec material may warp when heated above 140°F or when heated from one side only, it cannot be dry mounted or hot mounted.

## Laminating

Celtec is an ideal material for applications that require lamination. This section provides preparation information for the lamination process as well as detailed instructions for various types of laminations that can be used with Celtec.

Because prints are one of the most frequently laminated materials, the sections that follow will generally refer to the lamination of a print, although many other materials can be used.

**NOTE!**


Because Celtec material may warp when heated above 140°F or when heated from one side only, it cannot be used in any lamination process requiring heat.

## Adhesion

For best results, the Celtec material should be cleaned with isopropyl alcohol prior to adhesion and allowed to dry thoroughly.

When laminating with pressure-sensitive adhesives, a force of 25-40 psi is required (Figure 5b). Proper spacers are also critical. Since must be applied equally across the material, the top roll must move evenly from left to right while maintaining even contact between top and bottom laminating rolls.

To achieve even contact, or “zero the nip,” then use spacer shims to preset the nip opening for a particular laminate. Use sufficient pressure to completely eliminate any air bubbles between the Celtec material, the adhesive, and the print or other material.

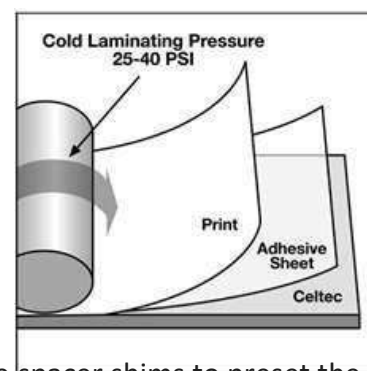

**Figure 5b**

# SPECIAL APPLICATIONS

CELTEC®

The lamination will achieve maximum bonding in three hours. If the lamination has been performed properly, the finished mount can be flexed without the print becoming loose in the center.

To prevent moisture from becoming trapped between layers of porous material (such as paper) and creating blisters, the level of moisture in both the material to be laminated and the atmosphere should be reduced before pressing. Some materials may require pre-drying. Celtec is nonporous and does not need pre-drying.

## NOTE!

Avoid hanging tacked pieces upside down for longer than 10 minutes as the prints may absorb moisture and change in dimension, causing bubbles and wrinkles in the finished product.

## Preventing Surface Blemishes

Surface blemished, such as wrinkles, can be caused by misalignment of the adhesive roll, too much pressure, or rollers that are not parallel. Trapped dirt or lumps of hardened adhesive common with Cibachrome or glossy prints may create small bumps in the finished product.

In order to prevent these problems, equipment used for Celtec lamination must be kept clean (Figure 5c). Use a fresh roll or sheet of transfer adhesive if bumps are caused by hardened adhesive. Dirt problems can be minimized by using an ionizing static eliminator.

Using prints or other materials made with a paper 0.007" or thicker can help prevent strike through.

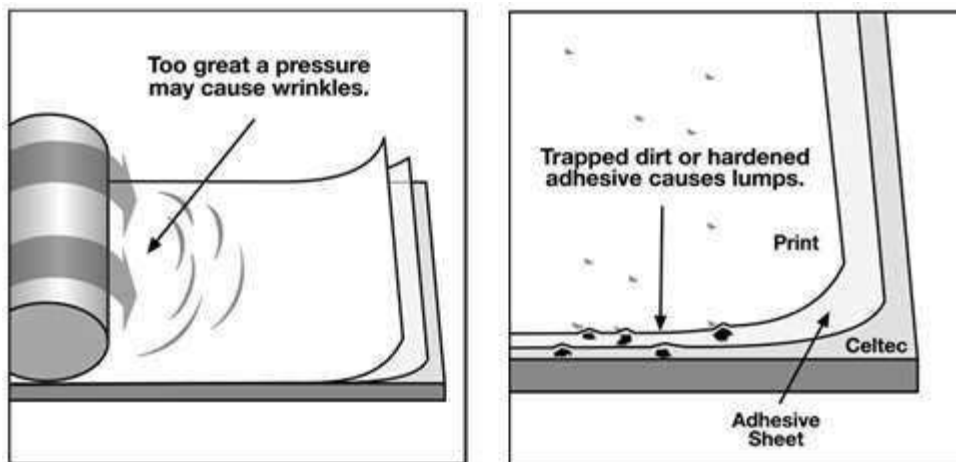


Figure 5c

**TIP!**

For best results, wipe down the back of the print and the face of the Celtec mount with a clean, dry cloth before it passes through the roll nip.

Whether the finished product is to be used indoors or outdoors, a clear, high-gloss overlay will help protect against fading as well as enhance the color. MACtac IP 7000 Perma Color overlay and Seal Print Shield have proven to work effectively with Celtec.

**NOTE!**

Do not use overlays, clear coatings, or sprays that contain solvents, as they may cause blistering.

## Laminating Techniques

Four techniques are recommended for laminating materials to Celtec, as described in the following sections. Depending upon the type of process applications and the equipment available, one or more of these processes may be appropriate for a particular application. None of these processes involves the use of heat. Because Celtec may warp at temperatures above 140°F or when heated from one side only, it cannot be dry mounted or hot mounted. The four recommended lamination techniques for Celtec are:

- Cold laminating with a press, using adhesive-backed paper
- Cold laminating using Vac-U-Mount press
- Hand laminating using transfer adhesive
- Hand laminating using spray adhesive

### Cold Laminating with a Press using Adhesive-Backed Paper

This process is most frequently used by commercial photo labs with Greig or Sealeze presses and transfer adhesives, such as MACtac IP 5000, Photomount, or Seal Print Mount. Either of two types of liner films, as a single-release liner film or a double-release liner film, can be used for this process. The basic process for laminating with a press using adhesive-backed paper is described in the following section.

# SPECIAL APPLICATIONS

CELTEC®

1. Set the roller pressure properly for the thickness of the pre-coated mounting substrate.
2. Place the mounting substrate on a flat surface and expose approximately 1" of the adhesive by peeling back the release paper (Figure 5d).
3. Carefully position the print on top of the substrate, using the folded release paper to prevent contact with the exposed adhesive (Figure 5e). Once positioned correctly, carefully apply the print to the exposed adhesive, pressing from the center toward the edges to ensure a smooth tack.

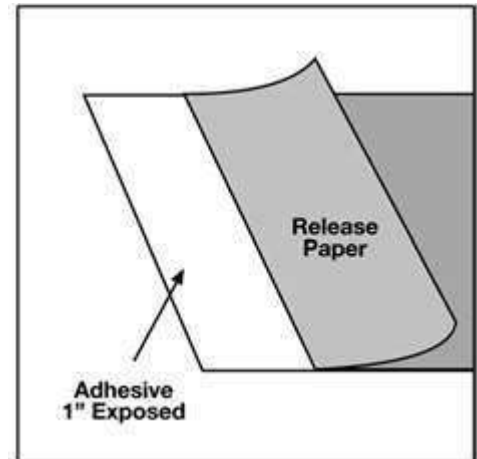


Figure 5d

4. Place the direction switch in the forward position and the speed control on medium.
5. Insert the materials to be processed into the laminator opening. Depress the foot switch and feed the substrate between the rollers until the pressure roller rests on the tacked portion of the material.
6. Hold the un-tacked portion of the print up and against the pressure roller. Depress the foot switch to feed the substrate through the rollers while peeling the release paper off the mounting substrate with one hand. To prevent wrinkles, the print must be held against the roller with the opposite hand while the substrate feeds through the press.
7. Remove the mounted print from the rear of the laminator and trim it to the required size.

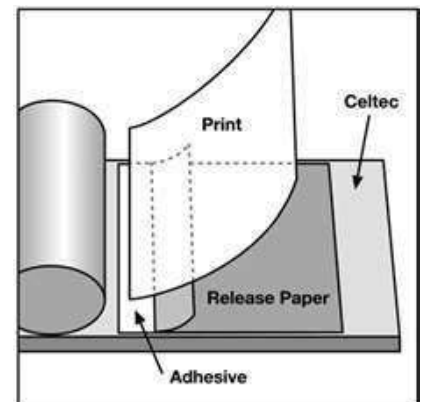


Figure 5e

## Coating using Single-Release Liner Films

1. Set the pressure properly for the thickness of the substrate(s) to be processed.
2. Load the supply roll of pressure-sensitive adhesive, such as Sealeze Print Mount.
3. Pull approximately 12" of adhesive film forward off the roll. Rest the film, adhesive side up, on top of the pressure roller.



4. Create a leader board by cutting a piece of substrate slightly larger than the width of the adhesive film and approximately 4" to 6" long. Lay the leader board across the film and smoothly adhere the bottom of the leader to the adhesive.
5. Place the direction switch in the forward position and the speed control on medium.
6. Pull the leader down and push it between the rollers. Depress the foot switch and feed the leader between the rollers approximately 3" to 4" inches. Be sure that the adhesive stays firmly adhered to the leader.
7. Once this process has been completed (referred to as "stringing the web") and the adhesive is feeding without wrinkles, the laminator is ready for production.
8. To coat, feed a substrate behind the leader board and between the rollers while depressing the foot switch. Feed until the substrate exits the rollers and automatically stops feeding. At this time, another substrate may be fed between the rollers for coating. This process is suitable for films with a paper release liner, such as Sealeze Print Mount, and leaves a 3/8" to 1/2" gap between the coated substrates to facilitate the trimming process.
9. After exiting the laminator, the coated substrate should be split apart and trimmed (Figure 5f).

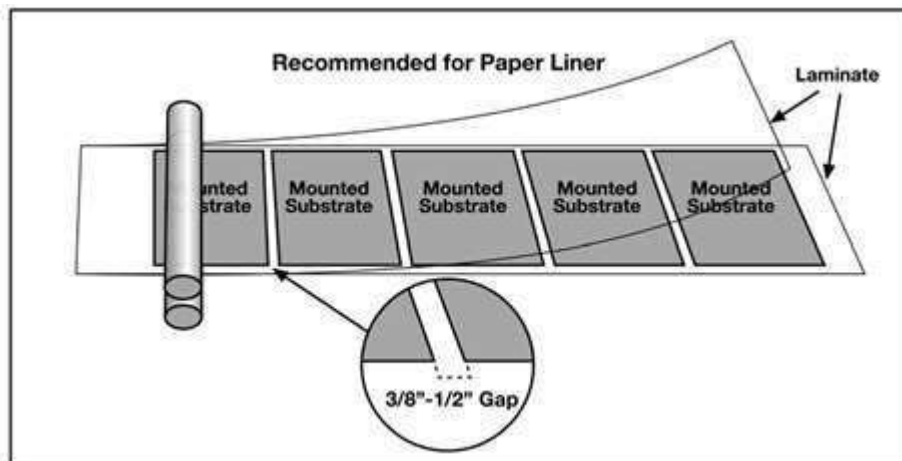


Figure 5f

## Coating using Double-Release Liner Films

Coating with double-release liner film, such as Sealeze OptiMount-UV or Print Mount Double, requires the use of a take-up mechanism to automatically remove and rewind one of the release liners during the coating procedure.

# SPECIAL APPLICATIONS

CELTEC®

1. Set the pressure properly for the thickness of the substrates to be processed.
2. Load the supply roll of pressure-sensitive adhesive, such as Sealeze OptiMount-UV.
3. Adhere double-stick tape or a pressure-sensitive film, such as Sealeze OptiMount-UV or Print Mount Double, to the surface of the take-up shaft.
4. Pull approximately 18" of adhesive film forward off the roll and adhere one release liner side smoothly to the take-up shaft, taking care to ensure that the film is square with the supply roll and no diagonal wrinkles are apparent (Figure 5g).

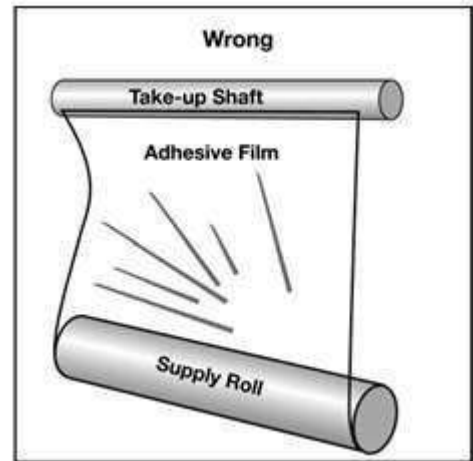


Figure 5g

5. Separate the adhesive film from the release liner secure to the take-up shaft and pull the adhesive film and remaining release liner down so that it rests adhesive side up on top of the pressure roller.
6. Lay a leader board the same thickness as the substrates to be used across the exposed adhesive film and smoothly adhere the bottom of the leader to the adhesive.

## Cold Laminating with VacuSEAL Press

This method is suggested for small- and medium-sized photo shops for mounting prints utilizing a spray adhesive, such as 3M Vac-U-Mount.

1. Spray the adhesive on the back of the piece to be mounted, keeping the spray 6" to 8" from the surface. If using a double coat of adhesive, the second coat should be applied in a direction perpendicular to the first coat. For bonding most art materials, the adhesive is typically applied only to one surface, usually the back of the print.
2. Allow the spray to dry two to four minutes before mounting so that the adhesive becomes tacky. If blisters occur from trapped solvent, allow the adhesive to dry slightly longer than four minutes.
3. Position the print on the Celtec material and place inside the VacuSEAL vacuum frame.
4. Apply vacuum for 10 minutes.

## Hand Laminating using Transfer Adhesive

For small shops or display makers without access to presses, this method can be used for lamination of flat, relatively small items utilizing a transfer adhesive (Figure 5h).

1. Using a sheet of transfer adhesive having both sides covered by release paper, peel away and fold back the release paper 1/2" inch from one edge.
2. Place the edge of the print to be laminated on the exposed adhesive.
3. Remove the rest of the release paper while lifting the print slightly to avoid contact with the adhesive, then use a roller or a squeegee to smooth the print evenly onto the adhesive.
4. With the face print down and the remaining release paper facing up, smooth out any excess air from between the print and the adhesive with a squeegee.
5. To laminate the print to the Celtec material, peel away and fold back the release paper 1/2" from one edge.
6. Placing the print evenly on the Celtec material, tack the exposed adhesive to the Celtec.
7. Gradually remove the liner while pressing closely with a hand roller or a squeegee to eliminate any air bubbles until the entire print has been laminated (Figure 5i).

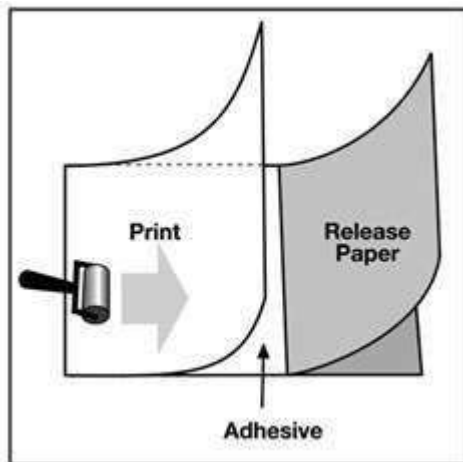


Figure 5h

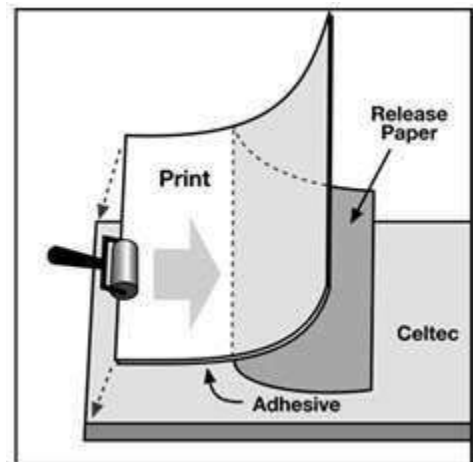


Figure 5i

### TIP!

For best results, remove only a small section of the liner at a time, approximately 12" or less, while adhering the print to the Celtec.


# SPECIAL APPLICATIONS

CELTEC®

## Hand Laminating using Spray Adhesive

For small shops or display makers without access to equipment, this method is recommended for the lamination of flat, relatively small items utilizing a spray adhesive, such as 3M Vac-U-Mount (Figure 5j).

Figure 5j

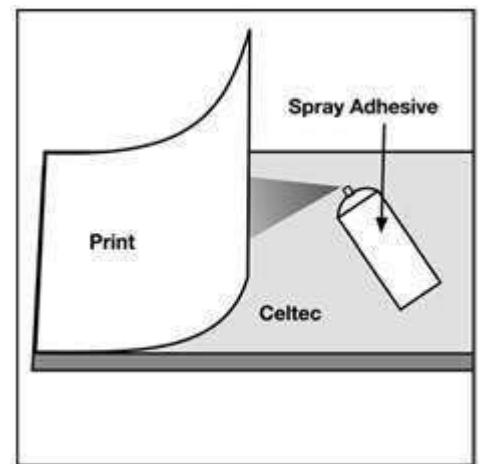

1. Spray the adhesive on the back of the piece to be mounted, keeping the spray 6" to 8" from the surface. If using a double coat of adhesive, the second coat should be applied in a direction perpendicular to the first coat. For bonding most art materials, the adhesive is typically applied only to one surface, preferably the back of the print.
2. Allow the spray to dry between two to four minutes before mounting so that the adhesive becomes tacky.
3. Place the adhesive side of the print or other item on the Celtec surface, pressing smoothly from the center of the piece to the edges in order to eliminate any wrinkles and trapped air immediately.
4. Place a clean sheet of Celtec over the laminated piece to weigh it down. Although the bond should be at a maximum strength after 15 minutes, allow 24 hours before exposing the piece to any sudden temperature or humidity changes.

## Delaminating

A print mount can be delaminated within five minutes if a pressure-sensitive adhesive, such as MACtac IP 5000 or Seat Print Mount, has been used. Although the print is usually ruined, the Celtec material can be reused.

If five minutes have already passed, a hot air gun or a hair dryer can be used to heat the material in order to peel off the lamination. Isopropyl alcohol or mineral spirits can be used to remove the remaining adhesive.

## Laminating Film Manufacturers

Company	Contact	Address
3M Adhesives Division <a href="http://www.3m.com">www.3m.com</a>	800.362.3550 F: 651.733.9175	3M Center, Building 21 St. Paul, MN 55144
DryTac Corporation <a href="http://www.drytac.com">www.drytac.com</a>	800.280.6013	5601 Eastport Boulevard Richmond, VA 23231
Henkel Adhesives <a href="http://www.henkel.com">www.henkel.com</a>	847.468.9200 F: 847.468.9819	1345 Gasket Drive Elgin, IL 60120
MACtac <a href="http://www.mactac.com">www.mactac.com</a>	866.262.2722	4560 Darrow Road Stow, OH 44224

## Photo-Mounting Press Manufacturers

Company	Contact	Address
Advanced Greig Laminators <a href="http://www.aglinc.com">www.aglinc.com</a>	800.276.2664	801 Burton Blvd Deforest WI, 53532
GBC <a href="http://www.GBC.com">www.GBC.com</a>	844.702.7170	Four Corporate Dr Lake Zurich, IL 60047

## Cold Mounting Laminator Manufacturers

Company	Contact	Address
Coda, Inc. <a href="http://www.codamount.com">www.codamount.com</a>	201.825.7400 F: 201.825.8133	30 Industrial Avenue Mahwah, NJ 07430

Field performance of Celtec indicates excellent weatherability in outdoor applications under various environmental conditions.

## **Weatherability / Effects of Outdoor Exposure**

### **Tensile Strength**

Virtually no tensile strength changes have been noted in prolonged environmental exposure tests.

### **Color**

Dark colors are not recommended because they absorb heat energy and can exceed use temperatures.

### **UV Stability of White Celtec**

One of the many advantages of Celtec expanded PVC sheet is its ultraviolet durability. Celtec is made from the same ingredients found in most weatherable vinyl siding and window material. While the concentration of these ingredients is not the same, Celtec will provide years of minimal color change. In addition, Celtec will not warp, rot, crack, or peel like wood products in similar outdoor exposures.

Celtec was weathered in a “QUV” weatherometer by Vista Chemical Company along with a standard pipe compound, vinyl siding, and another major expanded PVC brand. The test replicated two years of exposure outdoors in Arizona. Celtec in 3mm and 6mm thickness retained more of their respective color than the major competitors’ brands of expanded PVC sheet for the same thicknesses.

### **Stress**

Some silkscreen inks contain solvents that can cause environmental stress cracks. For more information, refer to the desired manufacturer’s ink and solvent charts.

## Fire Characteristics

Any material having an oxygen index in excess of 26% will not continue to burn when a flame source is removed. The oxygen index of Celtec is 35%, which makes it self-extinguishing, meaning that, when the flame source is removed, the burning stops. It is important to remember that many other plastic materials and natural products, such as wood, have values under 26%.

High-Oxygen Index: ASTM D-2863 measures the percent of oxygen in an oxygen/nitrogen mixture that barely supports burning. The oxygen content of the earth's atmosphere is about 21%. Materials with oxygen index values of approximately 28% and above should not continue burning after the flame source is removed because the normal atmospheric oxygen content is insufficient to support combustion.

## Impact Resistance and Environmental Stress


Effect of Temperature: With decreasing temperature, there is a tendency towards decreased impact resistance.

Samples of 3mm Celtec were placed in a freezer at temperature of -10°C for a period of 12 hours. The test bars were then impacted per ASTM D266 Charpy Impact - Test Method B (Specimens Un-Notched). The "Cold Break" specimens retained 85% of the original room temperature impact strength.

**Celtec 16X  
Magnification**




Surface

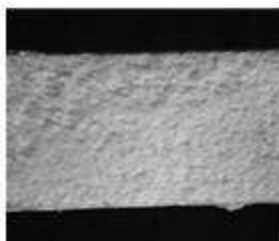


Cross-Section

**Other Leading  
Brands 16X  
Magnification**

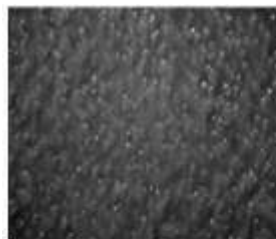


Surface

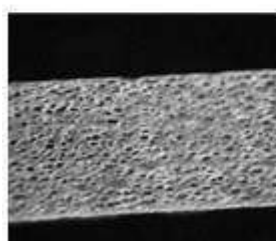

Cross-Section



Surface

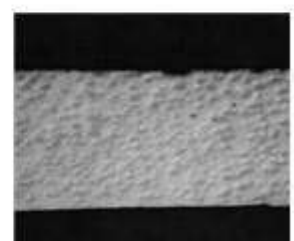

Cross-Section

# ENGINEERING SPECIFICATIONS

CELTEC®

## Cellular Foamed Vinyls

“There are two types of cellular foamed vinyls: open cell and closed cell. In the closed cell type, each cell is individual, usually spherical in shape, and completely enclosed by plastic walls. This type of cell structure has good insulating properties as well as a high degree of buoyancy. In the open cell type, all cells are interconnected. This type of cell structure is known for its absorbency and capillary action.”

Source: Encyclopedia of PVC; Vol. 2, Page 619.

A rigid foam PVC sheet or profile that is extruded via a free expansion process would thus be considered a closed cell foam. Examples of open cell types would be a foamable Plastisol or a sponge-like flexible plastic foam as is used in cushions or padding for furniture.

## Standard Specifications

### USDA Approved - Incidental Contact

Celtec can be used for sign needs wherever food is processed or sold. It is lead-, cadmium-, and barium-free.

### U.L. Classified

Celtec is the first foamed PVC to be U.L. Classified, meeting all three U.L. 1975 fire test requirements.

### Fire Characteristics

The oxygen index value of Celtec is 35%. Materials with a value of 28% or higher are considered self-extinguishing. For comparison, oak carries a value of 23% and birch a value of 21%.

### Health and Environmental

Celtec contains no lead, cadmium, barium, or zinc heat stabilizers. Celtec is made only with tin, which means that there are no special health, environmental, or waste disposal problems.



## ROHS

### **Celtec is RoHS compliant.**

RoHS is the acronym for Restriction of Hazardous Substances. RoHS, also known as Directive 2002/95/EC, originated in the European Union and restricts the use of specific hazardous materials found in electrical and electronic products. All applicable products in the EU market after **July 1, 2006**, must pass RoHS compliance.

The substances banned under RoHS are lead (Pb), mercury (Hg), cadmium (Cd), hexavalent chromium (CrVI), polybrominated biphenyls (PBB), and polybrominated diphenyl ethers (PBDE).

The restricted materials are hazardous to the environment, pollute landfills, and are dangerous in terms of occupational exposure during manufacturing and recycling.

# ENGINEERING SPECIFICATIONS

CELTEC®

## Celtec Typical Physical Properties

Property	Units	ASTM Method	Celtec 1MM - 30MM	Ultra White	DigiLite
<b>Physical</b>					
Density	g/cm <sup>3</sup>	D 792	0.55 - 0.7	1.42	0.47
Water Absorption	%	D 570/ D2842	0.15 - 0.3, 0.9	0.06	0.3%
Hardness, Shore D	Shore	D 2240	-	89	34
Rockwell Hardness	R Scale	D 785	-	115	
<b>Mechanical</b>					
Tensile Strength @ Yield	psi	D 638	2,256 - 3,000	411,000	1,500
Tensile Modulus	psi	D 638	144,000 - 232,000	-	111,000
Flexural Strength	psi	D 790	3,755	-	3,500
Yield Strength	psi	D 790	-	7,500	2,600
Flexural Modulus	psi	D 790	170,000	481,000	124,000
Yield Strength	psi	D 790	-	12,800	2,600
Izod Impact	ft-lb/in.	D 256	0.53	1	3mm – 0.61, 6mm -0.31
Nail Hold	lb./in.	D 1761	35	-	
Screw Hold	lb./in.	D 1761	680	-	
Staple Hold	lb./in.	D 1761	180	-	
Gardner Impact	in/lbs.	D 4228	103	-	
Charpy Impact (un-notched @ 23°)	ft-lb/in.	D 256	4.5 - 8.1	-	
<b>Thermal</b>					
Vicat Softening Point	°C	D 1525	-	83 / 181	73
Heat Deflection Temp @ 66 psi	°C	D 648	-	82 / 179	65
Heat Deflection Temp @ 264 psi	°C / °F	D 648	150	80 / 176	
Coefficient of Linear Expansion	in.in. °C	D 696	-	5.8 x 10 <sup>-5</sup>	
Coefficient of Linear Expansion	in./in. °F	D 696	3.2-4 x 10 <sup>-5</sup>	3.2 x 10 <sup>-5</sup>	3.2E-05
Thermal Conductivity	W/mK	D 177	0.084	-	

Property	Units	ASTM Method	Celtec 1MM - 30MM	Ultra White	DigiLite
<b>Flammability Ratings</b>					
Burning Rate	In/min		No burn when removed from flame		
Flame Spread Index	-	E 84	20	15	Current Product Covered
Vertical Burn Test	-	UL 94	5-V	V-0	
Flammability	-	UL 94V	-	Self-Extinguishing	Passed
Foam Fire Test	-	UL 1975	-	-	
Oil Canning (@ 140°)	°F	D 149	Passed	-	
<b>Electrical</b>					
Electrical Volume Resistivity	Ohm / cm	D 257	-	$5.4 \times 10^{15}$	
Dielectric Constant (60 Hz)	-	D 150	-	3.19	
Dissipation Factor (60Hz)	-	D 150	-	0.0096	
Loss Index (60 Hz)	-	D 150	-	0.03	
Dielectric Strength	volt / mil	D 149	112,000	544	
<b>Chemical</b>					
Chemical Resistance	-	D 1784	-	Class B	

Physical properties of plastic sheeting are represented as “Typical.” Information contained herein is considered accurate to the best of our knowledge. It is offered for your consideration and investigation and is not to be construed as a representation or warranty expressed or implied. Our warranties are limited to those expressly stated in formal contracts or in conditions of sale on our invoices and order acceptances. Conditions and methods of use may vary and are beyond the control of Vycom. Therefore, Vycom disclaims any liability incurred as a result of the use of this product in accordance with the data contained in our physical property charts. No information herein shall be construed as an offer of indemnity for infringement or as a recommendation to use the products in such a manner as to infringe any patent, domestic or foreign.

The “Typical” properties of our plastic sheet cannot be automatically used when engineering finished components, and the fabricator or end user is responsible for insuring the suitability of our products for their specific application or end use!

## Material Safety Data

Please visit Vycom's website for the following data: [Celtec Expanded PVC SDS](#)

1. Product Identification
2. Components and Hazard Classifications
3. Physical Data
4. Fire and Explosion Data
5. Health Hazard Information
6. Reactivity Data
7. Spill or Leak Procedures
8. Special Protection Information
9. Shipping, Transfer, and Storage

## Marketing Materials

Please visit Vycom's website for the following information: [Marketing Data](#)

1. Advertising
2. Images
3. Instructional Videos
4. Celtec Line Card - [Technical Resources](#)





**TOGETHER WE CAN MAKE A MORE SUSTAINABLE FUTURE.  
LET US RECYCLE YOUR SCRAP!**



### **WHAT WE RECYCLE**

**PVC, PE, and Acrylic**

**Printed and Unprinted Rigid PVC Sheets**

**End of Use Commercial and Retail Signage**

**Scraps and Drops from Cutting and Fabrication**

**Trade Show, Mobile Exhibits,  
Brand Environments, Marine, and More**

### **WE MAKE BEAUTIFUL, LONG LASTING, SUSTAINABLE PRODUCTS!**

**Vycom® PVC, HDPE, and PP Sheets**

**TimberTech® Decking**

**AZEK® Exteriors Trim Boards**



**All Scrap & Waste is Recycled  
& Repurposed in the USA**

For questions regarding types of materials recycled,  
pick up minimums and frequency, or simply how to get started,  
**please contact your local Vycom Representative.**



# WE TAKE SUSTAINABILITY SERIOUSLY.



## RECYCLING PROGRAM

RIGID PVC • ACRYLIC • HDPE

**Plastic waste is a global crisis.** As an overwhelming amount of PVC, Acrylic and PE are not properly recovered or recycled, performance plastics are valuable long after their initial usage. In a circular economy, performance plastics can be recycled again and again, eliminating waste and the continual use of resources. As affiliates of The AZEK Company, both Vycom and Return Polymers are proud to not only offer high-quality products made from up to 100% post-consumer and post-industrial recycled materials, we also play an active role in reducing plastic waste through recycling. Throughout The AZEK Company we are committed to being good corporate citizens and will continuously explore ways to keep performance plastics out of the waste stream.

## HOW RECYCLING WITH VYCOM WORKS

ALL AT NO COST TO YOU!

### 1 Contact Vycom to Enroll

Contact Vycom today at **RecyclingWithVycom@VycomPlastics.com** to enroll in the Vycom Recycling Program, which is designed to take back and recycle printed or unprinted rigid PVC, PE and Acrylic sheets, as well as scraps and drops from finishing and fabricating.

### 2 We Provide Bins & Totes

Once enrolled, we provide you with bulk containers to store your scrap and recycled materials.

**NOTE:** *Keep in mind, recycled materials must be separated by polymer; ie PVC and Acrylic can not be stored in the same bin.*

### 3 Schedule a Pick-Up

When it's time to schedule a pick-up: **please contact Return Polymers at Recycling@AzekCo.com**, who will coordinate retrieving your scrap after a pick-up date and time is agreed upon. We then replenish your bin stock so the process can continue without interruption.

### 4 Your Scrap & Waste is Recycled

After collection, your scrap and waste is recycled and repurposed into high quality raw materials used in the production of beautiful, long-lasting, sustainable products.

#### WHAT YOUR RECYCLED SCRAP MAKES:

- TimberTech Decking
- AZEK Exteriors Trim Boards
- Vycom PVC, HDPE and PP sheets

# VYCOM

WWW.VYCOMPLASTICS.COM





# VYCOM<sup>®</sup>

Vycom manufactures market-leading brands of highly innovative plastic sheet products designed to replace wood, metal and other traditional materials in a variety of applications. The company's extensive inventory and product offerings provide its customers with the convenience of single-source purchasing and the ability to maximize efficiencies. Vycom's manufacturing agility places it in a prime position to be the essential partner in creating solutions that optimize quality and performance, and in providing a more sustainable future.

**AN AFFILIATE OF THE AZEK<sup>®</sup> COMPANY**

**801 E. COREY STREET  
SCRANTON, PA 18505**

**PH: (800) 235-8320**

**FX: (800) 858-9266**

**[WWW.VYCOMPLASTICS.COM](http://WWW.VYCOMPLASTICS.COM)**



**MADE IN THE USA**